



Standard Test Method for Glow-Wire Ignition of Materials¹

This standard is issued under the fixed designation D 6194; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the minimum temperature required to ignite insulating materials using a glowing heat source. In a preliminary fashion, this test method differentiates between the susceptibilities of different materials with respect to their resistance to ignition due to an electrically-heated source.

1.2 This test method applies to molded or sheet materials available in thicknesses ranging from 0.25 to 6.4 mm.

1.3 This test method is not valid for determining the ignition behavior of complete electrotechnical equipment, since the design of the electrotechnical product influences the heat transfer between adjacent parts.

1.4 This test method measures and describes the response of materials, products, or assemblies to heat and flame under controlled conditions, but does not by itself incorporate all factors required for fire hazard or fire risk assessment of the materials, products, or assemblies under actual fire conditions.

1.5 The values stated in SI units are to be regarded as the standard. (See IEEE/ASTM SI-10 for further details.)

1.6 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. For specific precautionary statements, see Section 8.9.*

1.7 Fire testing of products and materials is inherently hazardous, and adequate safeguards for personnel and property shall be employed in conducting these tests. Fire testing involves hazardous materials, operations, and equipment.

NOTE 1—Although this test method and IEC 60695-2-1/3 differ in approach and in detail, data obtained using either are technically equivalent.

¹ This test method is under the jurisdiction of ASTM Committee D09 on Electrical and Electronic Insulating Materials and is the direct responsibility of Subcommittee D09.212 on Fire Performance Standards—Electrical Tests.

Current edition approved Nov. 10, 1997; Oct. 1, 2003. Published November 2003. Originally approved in 1997. Last previous edition approved in 19987 as D 6194 – 97.

2. Referenced Documents

2.1 *ASTM Standards:*²

~~D-1711 Definitions of Terms~~ 1711 Terminology Relating to Electrical Insulation

E 176 Terminology of Fire Standards

E 220 Test Method for Calibration of Thermocouples by Comparison Techniques

E 230 Specification and Temperature-Electromotive Force (EMF) Tables for Standardized Thermocouples

IEEE/ASTM SI-10 International System of Units (SI), The Modernized Metric System

2.2 *IEC Standard:*

~~IEC 60695-2-1/3: Fire Hazard Testing, Part 2: Testing—Section 20: Glowing/Hot-Wire Based Test Methods, Section 1: Glow-Wire Methods—Glow-Wire Coil Ignitability Test Method for Materials~~³

~~IEC 60695-4: Fire Hazard Testing—Part 4: Terminology Concerning Fire Tests~~³

2.3 *ISO Standard:*

~~ISO/IEC Guide 52: Glossary of Fire Terms and Definitions~~⁴

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards*, Vol 10.01, volume information, refer to the standard's Document Summary page on the ASTM website.

~~*Annual Book of ASTM Standards*, Vol 04.07.~~

³ Available from International Electrotechnical Commission (IEC), 3 Rue de Varembe, Geneva, Switzerland.

ISO 13943: Fire Safety—Vocabulary⁴

3. Terminology

3.1 Definitions:

3.1.1 Use Terminology E 176, ISO 13943, and ISO/IEC Guide 52 IEC 60695-4 for definitions of terms used in this test method and associated with fire issues. Where differences exist in definitions, those contained in Terminology E 176 shall be used. Use Terminology D 1711 for definitions of terms used in this test method and associated with electrical insulation materials.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *glow wire, n*—a wire of specified dimensions that can be controllably-heated electrically to determine ignitability of a material.

3.2.1.1 Discussion—Fig. 1 shows a glow wire and its positioning.

3.2.2 *ignition, n*—initiation of combustion.

3.2.2.1 Discussion—Ignition is deemed to have taken place when the first of the following occurs: sustained flaming on the test specimen surface for over 5 s or falling particles causing the appearance of flames on a tissue paper placed underneath the test specimen.

4. Significance and Use

4.1 Under certain conditions Summary of operation, or when malfunctions occur, it is possible that components of electrotechnical products become overheated. When Test Method


4.1 In this happens, a possible result is ignition of the adjacent insulation material.

4.2 This test method assesses method, the susceptibility of electrical insulating materials equipment being tested is exposed to ignition under such conditions.

4.3 This test method determines electrical heating from a glow-wire and the minimum temperature required glow-wire is heated to ignite a material by pre-determined temperature until the effect of a glowing heat source, under the conditions of test.

Annual Book of ASTM Standards, Vol 14.03.

⁴ Use undyed, soft, strong, lightweight tissue paper weighing between 12 and 30 g/m².

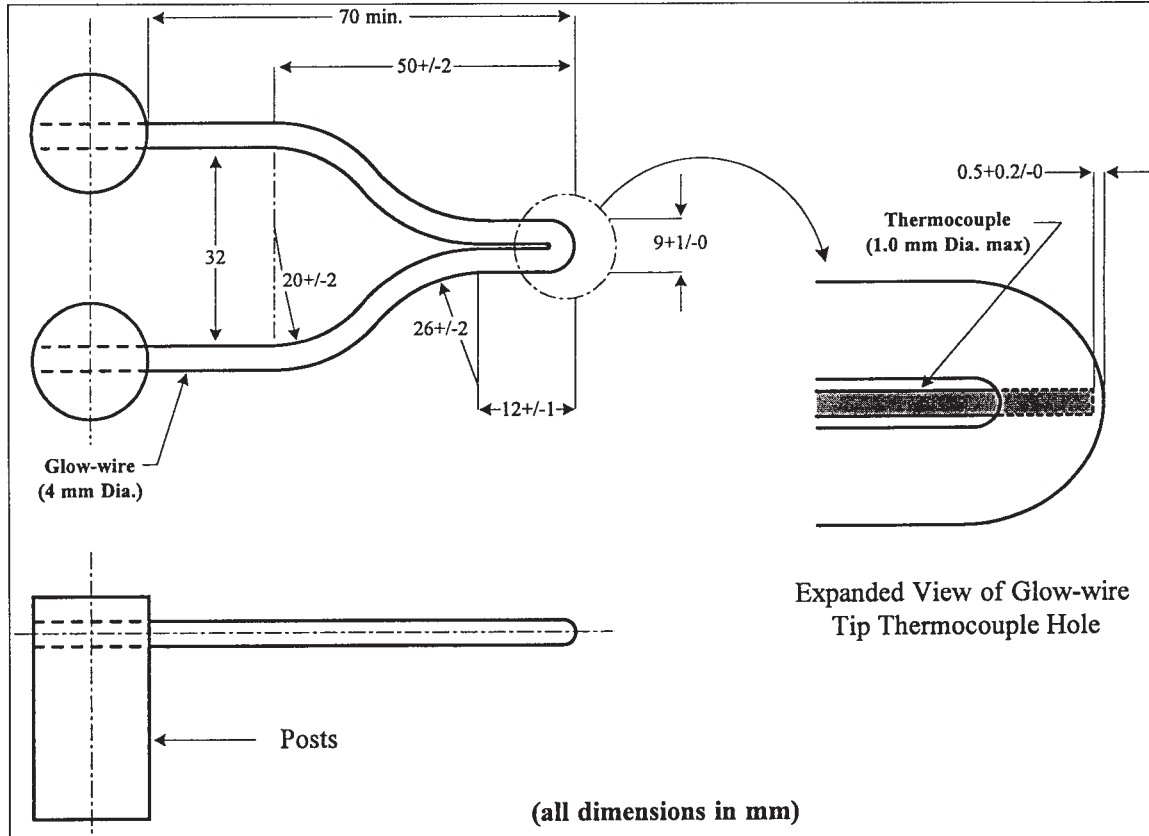

NOTE 1—All dimensions in millimetres.

FIG. 1 Glow-Wire and Positioning of the Thermocouple

~~4.4 Subject to limitations in precision and bias, this test method can be used to categorize materials. minimum temperature for glow-wire ignition is assessed.~~

5. Significance and Use

~~5.1 During operation of electrical equipment, including wires, resistors, and other conductors, it is possible for overheating to occur under certain conditions of operation, or when malfunctions occur. When this happens, a possible result is ignition of the adjacent insulation material.~~

~~5.2 This test method assesses the susceptibility of electrical insulating materials to ignition as a result of exposure to a glowing wire.~~

~~5.3 This test method determines the minimum temperature required to ignite a material by the effect of a glowing heat source, under the specified conditions of test.~~

~~5.4 This method is suitable, subject to the appropriate limitations of an expected precision of $\pm 15\%$, to categorize materials.~~

~~5.5 In this procedure, the specimens are subjected to one or more specific sets of laboratory conditions. If different test conditions are substituted or the end-use conditions are changed, it is not always possible by or from this test to predict changes in the fire-test-response characteristics measured. Therefore, the results are valid only for the fire test exposure conditions described in this procedure.~~

6. Apparatus

~~56.1 *Glow-Wire*—Nichrome wire (nominal 80 % nickel/20 % chromium) with—The glow-wire shall be a Nichrome (Nickel-Chrome) wire, that is iron free, with the following nominal ~~4.0 mm~~ properties: a wire composition of 20 % chromium-80 % nickel, a diameter of 4 mm, and it shall be formed to the dimensions shown in Fig. 1.~~

~~56.2 *Thermocouple*—A Use Type K sheathed fine-wire thermocouple, having an overall diameter of 1.0 mm max, and wires (Type K) of, for example, NiCr and NiAl suitable for continuous operation at temperatures up to 960°C, with the welded point located inside the sheath, is used for measuring the temperature of the glow-wire. Examples of suitable wire compositions are Nickel-Chromium (NiCr) and Nickel-Aluminum (NiAl).~~

~~56.2.1 *Construct the thermocouple sheath*—is made of a metal that will allow the thermocouple to perform its function in air at sheath temperatures of at least 1050°C. The Arrange the thermocouple is arranged in a pocket hole, drilled in the tip of the glow-wire, as shown in Fig. 1. Maintain the thermal contact between the walls of the bored hole in the glow-wire by pinning the sheathed thermocouple in place. The Ensure that the thermocouple must follow follows the movement of the tip of the glow-wire resulting from elongation caused by thermal heating.~~

~~56.3 *Temperature Indicator*—A Use a temperature indicator for Type K thermocouples capable of reading up to 1000°C. Calibrate the combination thermocouple and temperature indicator in accordance with the general procedures outlined in Test Method E 220. The initial calibration tolerance is defined in the tables of Specification and Temperature-Electromotive Force (EMF) Tables E 230.~~

~~56.4 *Supply Circuit*—A The supply circuit shall be capable of supplying up to 150 A at 2.1V, with smooth continuous adjustment of voltage to provide the required current as needed to maintain the desired glow-wire tip temperature.~~

~~56.5 *Test Fixture*—A fixture which will hold the glow-wire As shown in a horizontal plane and move it against the vertical test specimen, maintaining a force of $1.0 \pm 0.2\text{ N}$ over a distance of at least 7 mm (see Fig. 2).—, the test fixture shall be capable of holding the glow-wire in a horizontal plane and moving it against the vertical test specimen, maintaining a force of $1.0 \pm 0.2\text{ N}$ over a distance of at least 7 mm.~~

NOTE 2—A weight of $100 \pm 20\text{ g}$, as shown in Fig. 2, will provide the required force.

~~56.6 *Indicator Board*—A Use as indicator a flat pine wood board with a smooth finish, approximately 10 mm thick, and in close contact with a single layer of tissue paper,⁴ located at a distance of $200 \pm 5\text{ mm}$ below the glow-wire tip.~~

~~56.7 *Test Chamber*—A Use as a test chamber a closed draft-free chamber that permits observation of the specimen and has a volume of at least 0.3 m^3 . Provide a means for positive venting of the The test chamber shall be positively vented to the outside atmosphere of the test facility before and after the test, but it shall remain closed and for closing of the vent unvented during the test.~~

6. Test Specimen

~~6.1 Prepare square specimens that are approximately $60 \times 60\text{ mm}$ or round specimens that are approximately 60 mm in diameter, and of a thickness commonly encountered in practice. Thicknesses less than 0.25 mm or greater than 6.4 mm are not valid for this test method. Generally, ten specimens will suffice to complete the procedure specified in Section 8. test. The chamber shall be equipped with an observation window.~~

7. Conditioning

~~7.1 *Condition specimens, test board*Test Specimen~~

~~7.1 Prepare square specimens that are approximately $60 \times 60\text{ mm}$ or round specimens that are approximately 60 mm in diameter, and tissue paper at $23 \pm 2^\circ\text{C}$ and $50 \pm 5\%$ relative humidity of a thickness commonly encountered in practice.~~

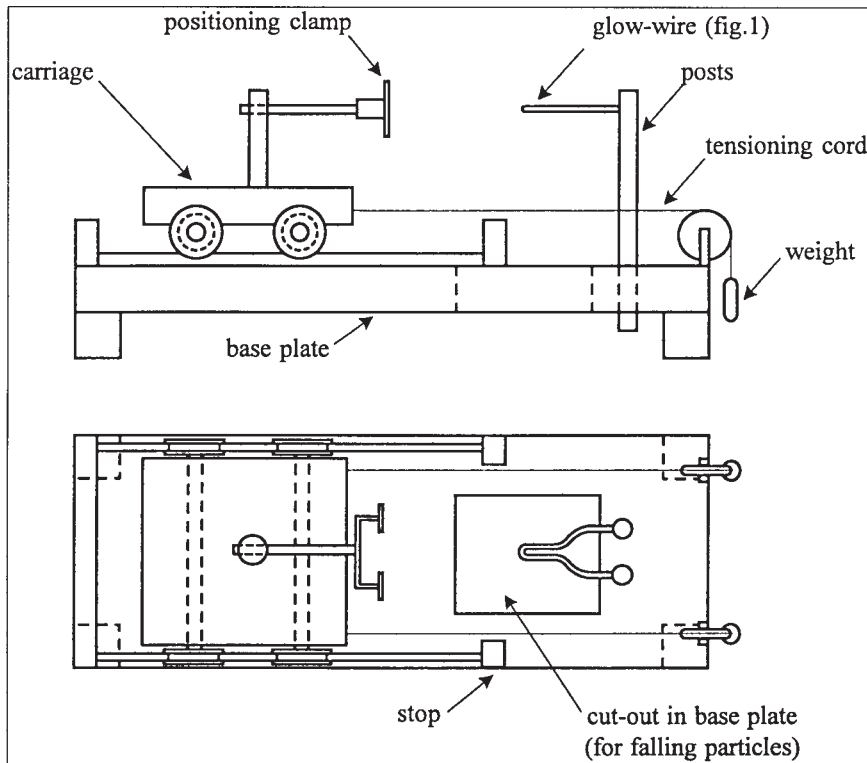


FIG. 2 Test Apparatus (Example)

Thicknesses less than 0.25 mm or greater than 6.4 mm are not valid for at least 40 h prior this test method. Generally, ten specimens will suffice to complete the procedure specified in Section 9.

8. Safety Precautions

8.1 It is possible that fumes Conditioning

8.1 Condition specimens, test board and products of incomplete combustion are liberated from the specimen when conducting this test. Avoid the inhalation of such fumes tissue paper at $23 \pm 2^\circ\text{C}$ and products of combustion and exhaust them from the test chamber after each run.

8.2 Take precautions $50 \pm 5\%$ relative humidity for at least 40 h prior to safeguard the health of personnel against the risk of explosion or fire, the inhalation of smoke, or other products of combustion, or the exposure to the residues potentially remaining on the specimen after testing.

9. Safety Precautions

9.1 It is possible that fumes and products of incomplete combustion are liberated from the specimen when conducting this test. Avoid the inhalation of such fumes and products of combustion and exhaust them from the test chamber after each run.

9.2 Take precautions to safeguard the health of personnel against the risk of explosion or fire, the inhalation of smoke, or other products of combustion, or the exposure to the residues potentially remaining on the specimen after testing.

10. Procedure

910.1 Before each test, clean the tip of the glow-wire with a wire brush to remove any residue left from previously tested materials.

910.2 Mount the specimen in the test fixture so that the surface that comes in contact with the tip of the glow-wire is vertical and any heat losses to the supporting means are insignificant. Adjust the equipment so the depth of penetration is limited to 7 mm below the surface of the specimen. Shield the specimen during the heating of the glow-wire.

910.3 Close the chamber vents and doors, making the test chamber draft free and heat the glow-wire to the pre-determined temperature. Use the calibrated thermocouple to record the glow-wire temperature. Maintain the pre-selected glow-wire temperature for at least 60 s prior to conducting the test.

910.4 Bring the specimen in contact with the tip of the glow-wire at an applied force of $1.0 \pm 0.2\text{ N}$ for $30 \pm 1\text{ s}$.

NOTE 3—The glow-wire temperature will decrease when the tip contacts the test specimen.

910.5 Observe to see whether ignition occurs during the application of the glow-wire (see 3.2.1). For the purposes of this test, ignition will be deemed to have occurred if either sustained flaming occurs (appearance of a flame on the surface of the test

specimen which lasts for more than 5 s) or the tissue paper on the indicator board placed underneath the apparatus exhibits flames caused by particles falling from the test specimen.

910.5.1 If ignition occurs, repeat the test with a new test specimen, and at a temperature 50°C lower than that used during the previous test. If the resulting temperature has already been used, do not retest at that temperature.

910.5.2 If ignition does not occur, repeat the test with a new test specimen, and at a temperature 50° higher than that used during the previous test. If the resulting temperature has already been used, do not retest at that temperature.

910.6 When a maximum temperature has been determined, following the procedure in 910.5, repeat the test with a new test specimen with a temperature interval of 25°C, in the final approach to determine the maximum test temperature which will not cause ignition during three consecutive tests.

910.7 The glow-wire ignition temperature is that temperature that is 25°C higher than the highest temperature at which the tip of the glow-wire does not cause ignition during three consecutive tests.

10. Report

10.1 Report the following information:

10.1.1 Complete identification of the material tested including type, source, and manufacturer's code number,

10.1.2 Thickness of specimens tested, and

10.1.3 The glow-wire ignition temperature.

11. Report

11.1 Report the following information:

11.1.1 Complete identification of the material tested including type, source, and manufacturer's code number,

11.1.2 Thickness of specimens tested, and

11.1.3 The glow-wire ignition temperature.

12. Precision and Bias

142.1 *Precision*—It is not possible to specify the precision of the procedure in this test method for measuring the glow-wire ignition temperature because insufficient data has been developed and compiled for a reliable statistical analysis.

142.2 *Bias*—No information can be presented on the bias of the procedure in this test method for measuring the glow-wire ignition temperature because no material having an acceptable reference value is available.

123. Keywords

123.1 electrically heated sources; flame; glow-wire; ignitability; ignition; plastic electrical insulating materials

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).