



Designation: D 4956 – 001a

## Standard Specification for Retroreflective Sheeting for Traffic Control<sup>1</sup>

This standard is issued under the fixed designation D 4956; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This standard has been approved for use by agencies of the Department of Defense.*

### 1. Scope

1.1 This specification covers flexible, non-exposed glass bead lens and microprismatic, retroreflective sheeting designed for use on traffic control signs, delineators, barricades, and other devices.

1.2 The values stated in inch-pound units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 The following safety hazards caveat pertains only to the test methods portion, Section 7, of this specification. *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:

---

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D04 on Road and Paving Materials and is the direct responsibility of Subcommittee D04.38 on Highway Traffic Control Materials.

Current edition approved Jan. Aug. 10, 2000<sup>1</sup>. Published April 2000. September 2001. Originally published as D 4956 – 89. Last previous edition D 4956 – 99<sup>01</sup>.

- B 209 Specification for Aluminum and Aluminum-Alloy Sheet and Plate<sup>2</sup>  
 B 209M Specification for Aluminum and Aluminum-Alloy Sheet and Plate [Metric]<sup>2</sup>  
~~B 449 Practice 449 Specification for Chromate Treatments Chromates on Aluminum<sup>3</sup>~~  
 D 523 Test Method for Specular Gloss<sup>4</sup>  
 E 284 Terminology of Appearance<sup>4</sup>  
 E 308 Practice for Computing the Colors of Objects by Using the CIE System<sup>4</sup>  
 E 808 Practice for Describing Retroreflection<sup>4</sup>  
 E 810 Test Method for Coefficient of Retroreflection or Retroreflective Sheeting<sup>4</sup>  
 E 991 Practice for Color Measurement of Fluorescent Specimens<sup>4</sup>  
 E 1164 Practice for Obtaining Spectrophotometric Data for Object-Color Evaluation<sup>4</sup>  
 E 1347 Test Method for Color and Color-Difference Measurement by Tristimulus (Filter) Colorimetry<sup>4</sup>  
 E 1349 Test Method for Reflectance Factor and Color by Spectrophotometry Using Bidirectional Geometry<sup>4</sup>  
 G 7 Practice for Atmospheric Environmental Exposure Testing of Nonmetallic Materials<sup>5</sup>  
~~G 23 Practice for Operating Light-Exposure Apparatus (Carbon-Arc Type) With and Without Water for Exposure of Nonmetallic Materials<sup>5</sup>~~  
~~G 147 Practice 147 Practice for Conditioning and Handling of Nonmetallic Materials for Natural and Artificial Weathering Tests<sup>5</sup>~~  
~~G 1521 Practice for Operating Open-Flame Carbon-Arc Light Apparatus for Exposure of Exposing Nonmetallic Materials in Accelerated Test Devices that Use Laboratory Light Sources<sup>5</sup>~~  
 G 152 Practice for Operating Open Flame Carbon Arc Light Apparatus for Exposure of Nonmetallic Materials<sup>5</sup>  
 G 153 Practice for Operating Enclosed Carbon Arc Light Apparatus for Exposure of Nonmetallic Materials<sup>5</sup>  
 2.2 *Federal Specifications:*  
 FP-92 Standard Specifications for Construction of Roads and Bridges on Federal Highway Projects<sup>6</sup>  
 L-S-300C Federal Specification for Sheeting and Tape, Reflective: Non Exposed Lens<sup>7</sup>  
 2.3 *AASHTO Specification:*  
 M 268-8400 I<sup>8</sup>

### 3. Terminology

3.1 *Definitions*—Definitions of terms are as described in Terminology E 284 and Practice E 808.

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *reboundable sheeting, n*—retroreflective material intended to be attached to flexible impact resistant plastic devices, such as traffic drum-like channelizing devices.

### 4. Classification

4.1 Retroreflective sheeting shall consist of a white or colored sheeting having a smooth outer surface and that essentially has the property of a retroreflector over its entire surface. There are ~~six~~ nine types and five classes of retroreflective sheeting. Types are determined by conformance to the retroreflectance, color, and durability requirements listed in 6.1 and may be of any construction providing that those requirements are met. Type designation is provided as a means for differentiating functional performance. Typical examples of materials and applications are provided for descriptive information only and are not intended to be limitations or recommendations. Common identifiers for each type are listed in 4.2.

4.1.1 The typical applications for the retroreflective sheeting addressed in this specification are:

Type	Typical Application
I	Highway Signing, construction-zone devices, and delineators
II	Highway Signing, construction-zone devices, and delineators
III	Highway Signing, construction-zone devices, and delineators
IV	Highway Signing, construction-zone devices, and delineators
V	Delineators
VI	Temporary roll-up signs, warning signs, traffic cone collars, and post bands
VII	Highway Signing, construction-zone devices, and delineators
VIII	Highway Signing, construction-zone devices, and delineators
IX	Highway Signing, construction-zone devices, and delineators

<sup>2</sup> Annual Book of ASTM Standards, Vol 02.02.

<sup>3</sup> Annual Book of ASTM Standards, Vol 02.05.

<sup>4</sup> Annual Book of ASTM Standards, Vol 06.01.

<sup>5</sup> Annual Book of ASTM Standards, Vol 14.024.

<sup>6</sup> Available from Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.

<sup>7</sup> Available from General Services Administration, 470 East L'Enfant Plaza S.W., Suite 8100, Washington, DC 20407.

<sup>8</sup> Available from the American Association of State Highway and Transportation Officials, 444 N. Capitol St., N.W., Washington, DC 20001.

4.2 Retroreflective sheeting shall be classified as follows:

4.2.1 *Type I*—A medium-intensity retroreflective sheeting referred to as “engineering grade” and typically enclosed lens glass-bead sheeting. Typical applications for this material are permanent highway signing, construction zone devices, and delineators.

4.2.2 *Type II*—A medium-high-intensity retroreflective sheeting sometimes referred to as “super-engineering engineer grade” and typically enclosed lens glass-bead sheeting. Typical applications for this material are permanent highway signing, construction zone devices, and delineators.

4.2.3 *Type III*—A high-intensity retroreflective sheeting, that is typically encapsulated glass-bead retroreflective material. Typical applications for this material are permanent highway signing, construction zone devices, and delineators.

4.2.4 *Type IV*—A high-intensity retroreflective sheeting. This sheeting is typically an unmetallized microprismatic retroreflective element material. Typical applications for this material are permanent highway signing, construction zone devices, and delineators.

4.2.5 *Type V*—A super-high-intensity retroreflective sheeting. This sheeting is typically a metallized microprismatic retroreflective element material. This sheeting is typically used for delineators.

4.2.6 *Type VI*—An elastomeric high-intensity retroreflective sheeting without adhesive. This sheeting is typically a vinyl microprismatic retroreflective material. This sheeting is typically used for orange temporary roll-up warning signs, traffic cone collars, and post bands.

4.2.7 *Type VII*—A super-high-intensity retroreflective sheeting having highest retroreflectivity characteristics at long and medium road distances as determined by the  $R_A$  values of Table 1 at 0.1° and 0.2° observation angle. This sheeting is typically an unmetallized microprismatic retroreflective element material. Typical applications for this material are permanent highway signing, construction zone devices, and delineators.

4.2.8 *Type VIII*—A super-high-intensity retroreflective sheeting having highest retroreflectivity characteristics at long and medium road distances as determined by the  $R_A$  values of Table 2 at 0.1° and 0.2° observation angle. This sheeting is typically an unmetallized microprismatic retroreflective element material. Typical applications for this material are permanent highway signing, construction zone devices, and delineators.

4.2.9 *Type IX*—A very-high-intensity retroreflective sheeting having highest retroreflectivity characteristics at short road distances as determined by the  $R_A$  values of Table 3 at 1° observation angle. This sheeting is typically an unmetallized microprismatic retroreflective element material. Typical applications for this material are permanent highway signing, construction zone devices, and delineators.

**TABLE 11 Outdoor WTypeat VII Shering Photometric Requirements forg**  
All Climates

Typ Observation Angle	MoEnts Angle	Minimum Coefficient	Yentll of Rw	Gre reflection; Orange	RA-ed	Blue
I	24 <sup>B</sup>	50 % of Table 4				
-4°	II	750	3675 100	200	45	
-4°	II	750	375 100	200	45	
0.1° <sup>B</sup>	65 % of Table 30 <sup>B</sup>	570	430 215	57	115	26
0.1° <sup>B</sup>	+ 30°	570	430 215	57	115	26
III	36 <sup>B</sup>	750	560 280	75	150	34
IV	- 4°	430	320 160	43	86	20 % of Table 5
IV	36 <sup>B</sup>	430	320 160	43	86	20 % of Table 5
V	+ 30°	430	320 160	43	86	20 % of Table 5
V	36 <sup>B</sup>	240	180 90	24	48	11 % of Table 7
VI	- 6°	240	180 90	24	48	11 % of Table 7
VI	6	135	100 50	14	27	6.0 % of Table 9

<sup>A</sup>Test Method at minimum Coefficient intervals may be determined on Retro-reflective sheeting ( $R_A$ ) cd·l-inforx<sup>-1</sup>·mation<sup>-2</sup>.

<sup>B</sup>When Values are specified for 0.1° observation angle, yellow, or whites are supplied for constant request work-zonements that shall apply only when specified by the purchaser in writing time will be 12 m contract or order.

**TABLE 1 2 Type VIII Sheeting<sup>A</sup>**

Observation Angle	Entrance Angle	White	Yellow	Orange	Green	Red	Blue	Brown
0.2°	-4°	7.0	50	2.5	9.0	14	4.0	1.0
0.1° <sup>B</sup>	-4°	1000	750	375	100	150	60	30
0.2°	+30°	3.0	22	7.0	3.5	6.0	1.7	0.3
0.1° <sup>B</sup>	+30°	460	345	7.0	46	6.0	28	14
0.5°	-4°	3.0	25	13	4.5	7.5	2.0	0.3
0.2°	-4°	700	525	265	70	7.5	42	21
0.5°	+30°	1.5	13	4.0	2.2	3.0	0.8	0
0.2°	+30°	325	245	4.0	33	3.0	20	10
0.5°	-4°	250	190	94	25	38	15	7.5
0.5°	-4°	250	190	94	25	38	15	7.5
0.5°	+30°	115	86	43	12	17	7	3.5

<sup>A</sup> Minimum Coefficient of Retroreflection ( $R_A$ )  $\text{cd}/\text{ft}^2 \cdot \text{lx}^2 \cdot \text{m}^{-2}$  ( $\text{cd}/\text{lx} \cdot \text{m}^{-2}$ ).  
<sup>B</sup> Values for 0.1° observation angle are supplementary requirements that shall apply only when specified by the purchaser in the contract or order.

**TABLE 2 3 Luminance Type IX Sheeting (Y%) (Daytime Luminance)<sup>A</sup>**

Observation Angle	Entrance Angle	White	Yellow	Orange	Green	Red	Blue	Brown
White		27	500	250	66	130	30	
0.1° <sup>B</sup>	-4°	660	500	250	66	130	30	
... <sup>B</sup>	+30°	370	280	140	37	74	17	
Yellow		15	285	45	38	76	17	
0.2°	-4°	380	285	45	38	76	17	
Orange		14	30	82	22	43	10	
0.2°	+30°	215	30	82	22	43	10	
Green		3.0	180	9.0	24	48	11	
0.5°	-4°	240	180	9.0	24	48	11	
Red		2.5	12	50	14	27	6.0	
0.5°	+30°	135	12	50	14	27	6.0	
Blue		1.0	60	10	8.0	16	3.6	
1.0°	-4°	80	60	10	8.0	16	3.6	
Brown		4.0	9.0	17	4.5	9.0	2.0	
1.0°	+30°	45	9.0	17	4.5	9.0	2.0	

<sup>A</sup> Minimum Coefficient of Retroreflection ( $R_A$ )  $\text{cd}/\text{lx}^2 \cdot \text{m}^{-2}$ .  
<sup>B</sup> Values for 0.1° observation angle are supplementary requirements that shall apply only when specified by the purchaser in the contract or order.

**NOTE 1**—All retroreflective sheetings, but especially microprismatic sheetings, may have unique performance characteristics outside of the range of the standard geometries presented in the tables that define the types. Certain applications may require the use of a particular product within a particular type in order to achieve a desired level of retroreflectivity in a given situation. In these cases, information concerning additional performance characteristics must be obtained.

4.3 **Backing Classes**—The backing required for retroreflective sheeting Types I through IX shall be classified as follows:

4.3.1 **Class 1**—The adhesive backing shall be pressure-sensitive, require no heat, solvent, or other preparation for adhesion to smooth, clean surfaces.

4.3.2 **Class 2**—The adhesive backing shall have an adhesive that shall be activated by applying heat and pressure to the material. The temperature necessary to form a durable permanent bond shall be a minimum of 150°F (66°C).

4.3.2.1 The Class 2 material shall be repositionable under normal shop conditions and at substrate temperatures up to 100°F (38°C) and without damage to the material. The Class 2 material may be perforated to facilitate removal of air in heat-vacuum laminators, but the perforations must be of a size and frequency such that they do not cause objectionable blemishes when the sheeting is printed.

4.3.3 **Class 3**—The adhesive backing shall have a positionable low-tack pressure-sensitive adhesive that requires no heat, solvent, or other preparation for adhesion to smooth, clean surfaces. It shall be repositionable up to a temperature of 100°F (38°C) without damage to the material.

4.3.4 **Class 4**—The adhesive backing shall have a low-temperature pressure-sensitive adhesive that permits sheeting applications at temperatures down to +20°F (-7°C) without the aid of heat, solvent, or other preparation for adhesion to smooth, dry, clean surfaces.

4.3.5 **Class 5**—This shall be a nonadhesive backing made of material commercially used for self-supporting products such as traffic cone collars, temporary roll-up warning signs, and post bands.

## 5. Ordering Information

5.1 The purchaser using this specification shall include the following information:

5.1.1 ASTM designation (D 4956),

- 5.1.2 Classification type (see Section 4),
- 5.1.3 Adhesive class (see 4.3),
- 5.1.4 Daytime color (see 6.3),
- 5.1.5 Length and width of sheets (see 8.1),
- 5.1.6 Length and width of rolls (see 8.2), and
- 5.1.7 Supplementary information, if required by the purchaser.

5.1.7.1 Compliance with the minimum coefficient of retroreflection for 0.1° observation angle is a supplementary requirement which shall apply only when specified. An observation angle of 0.1° may be specified where the long distance performance of a sheeting is to be a requirement,

- 5.1.7.2 Fungus-resistance testing requirements (see Supplementary Requirement S1),
- 5.1.7.3 Reboundable sheeting requirements (see Supplementary Requirement S2),

5.1.8 Indication that the sheeting is intended for work zone use, if applicable, to determine which weathering requirements apply, and

- 5.1.89 Any additional information.

## 6. Performance Requirements

6.1 This is a summary of the minimum performance requirements for each type of retroreflective sheeting.

6.1.1 Type I—Minimum Coefficient of Retroreflection—Table 4; Outdoor Weathering—24 months, see 6.4; Reflectance or Daytime Luminance Factor—Table 2 5; Other requirements: When the colors orange, yellow, or white are specified for construction work zone applications, the outdoor weathering will be 12 months.

6.1.2 Type II—Minimum Coefficient of Retroreflection—Table 3; 6; Outdoor Weathering—36 months, see 6.4; Reflectance or Daytime Luminance Factor—Table 2 5; Other requirements: When the colors orange, yellow, or white are specified for construction work zone application, the outdoor weathering will be 12 months.

6.1.3 Type III—Minimum Coefficient of Retroreflection—Table 4; 7; Outdoor Weathering—36 months, see 6.4; Reflectance or Daytime Luminance Factor—Table 2 5; Other Requirements: When the colors orange, yellow, or white are specified for construction work zone applications, the outdoor weathering will be 12 months.

6.1.4 Type IV—Minimum Coefficient of Retroreflection—Table 5; 8; Outdoor Weathering—36 months, see 6.4; Reflectance or Daytime Luminance Factor—Table 6 9; Other Requirements: When the colors orange, yellow, or white are specified for construction work zone applications, the outdoor weathering will be 12 months.

6.1.5 Type V—Minimum Coefficient of Retroreflection—Table 7; 10; Outdoor Weathering—36 months, see 6.4; Reflectance or Daytime Luminance Factor—Table 8 11; Other requirements: When the colors orange, yellow, or white are specified for construction work zone applications, the outdoor weathering will be 12 months.

6.1.6 Type VI—Minimum Coefficient of Retroreflection—Table 9; 12; Outdoor Weathering—6 months, see 6.4; Daytime Luminance Factor—Table 5.

6.1.7 Type VII—Minimum Coefficient of Retroreflection—Table 1; Outdoor Weathering—36 months, see 6.4; Daytime Luminance Factor—Table 9; Other requirements: When the colors orange, yellow, or white are specified for construction work zone application, the outdoor weathering will be 12 months.

6.1.8 Type VIII—Minimum Coefficient of Retroreflection—Table 2; Outdoor Weathering—36 months, see 6.4; Daytime Luminance Factor—Table 9; Other requirements: When the colors orange, yellow, or white are specified for construction work zone application, the outdoor weathering will be 12 months.

6.1.9 Type IX—Minimum Coefficient of Retroreflection—Table 3; Outdoor Weathering—36 months, see 6.4; Daytime Luminance Factor—Table 9; Other requirements: When the colors orange, yellow, or white are specified for construction work zone application, the outdoor weathering will be 12 months.

6.2 Coefficient of Retroreflection—The coefficient of retroreflection shall meet or exceed the minimum requirements of Table 4; Tables 3-5; 1-4, Table 6, Table 7, Table 8, Table 10, and Table 9 12 as specified in 7.3.

6.3 Daytime Color— The color of the sheeting shall conform to requirements of Table 10 13 and one of the following Table 2; 5, Table 6; 9, or Table 8 11 when tested in accordance with 7.4. Daytime and nighttime color shall have substantially the same hue.

**TABLE 3 4 Type I Sheetin<sup>A</sup>**

Observation Angle	Entrance Angle	White	Yellow	Orange	Green	Red	Blue	Brown
0.2°	-4°	140	100	60	30	30	40	5.0
0.2°	-4°	70	50	25	9.0	14	4.0	1.0
0.2°	+30°	60	36	22	1 0	12	4.0	2.7 0
0.2°	+30°	30	36	22	7.0	3.5	4.0	1.7 0.3
0.5°	-4°	50	33	20	9.0	10	3.0	2.0
0.5°	-4°	30	25	20	13	4.5	3.0	2.0 0.3
0.5°	+30°	28	20	12	6.0	6.0	2.0	1.8 0
0.5°	+30°	15	13	12	6.0	2.2	2.0	0.8 0.2

<sup>A</sup> Minimum Coefficient of Retroreflection (  $R_A$ )  $cd/ft^2(cd \cdot lx^{-1} \cdot m^{-2})$ .

**TABLE 4 5 TDaype III Sheetime Lumingance Factor (Y %) <sup>A</sup>**

ObservatiCon Angleor	EMintrance Angleimum	White	Yellow	OrMange	Green	Red	Blximue	Brow
—0.1° <sup>B</sup>	—4°	300	200	120	54	54	24	14
White	—4°	300	200	120	54	54	27	
—0.1° <sup>B</sup>	+30°	180	120	72				
Yellow	15	180	120	72				
32	32	14	1	0				
Orange	32	14	30					
—0.2°	—4°	250	170	100	45	45	20	12
Green	—4°	250	170	100	45	45	3.0	
—0.2°	+30°	150	100	—60	25	25	11	8.5
Red	+30°	150	100	—60	25	25	2.5	8.5
—0.5°	—4°	—95	—62	—30	15	15	7.5	5.0
Blue	—4°	—95	—62	—30	15	15	1.0	5.0
—0.5°	+30°	—65	—45	—25	10	—10	5.0	3.5
Brown	+30°	—65	—45	—25	10	—10	4.0	3.5

<sup>A</sup>Minimum Coefficient of Retroreflection ( $R_A$ )  $cd/ft^2(cd \cdot lx^{-1} \cdot m^{-2})$ .

<sup>B</sup>Values for 0.1° observation angle are supplementary requirements that shall apply only when specified by the purchaser in the contract or order.

**TABLE 5 6 Type IV<sub>1</sub> Sheeting <sup>A</sup>**

Observation Angle	Entrance Angle	White	Yellow	Orange	Green	Red	Blue	Brown
—0.1° <sup>B</sup>	—4°	400	270	160	—56	—56	—32	12
0.2°	—4°	140	100	60	30	30	10	5.0
—0.1° <sup>B</sup>	+30°	120	75	48	13	13	7	3.0
0.2°	+30°	120	75	48	22	10	12	3.0
—0.2°	—4°	250	170	100	—35	—35	—20	—7.0
—0.2°	+30°	—80	—54	—34	—9	—9	—5.0	—2.0
0.5°	+30°	80	54	20	9	10	5.0	2.0
—0.5°	—4°	135	100	64	—17	—17	—10	4.0
0.5°	—4°	135	100	64	—17	—17	—10	4.0
—0.5°	+30°	—55	—37	—22	6.5	6.5	3.5	1.4
0.5°	+30°	—55	—37	—22	6.5	6.5	3.5	1.0

<sup>A</sup> Minimum Coefficient of Retroreflection ( $R_A$ )  $cd/ft^2(cd \cdot lx^{-1} \cdot m^{-2})$ .

<sup>B</sup>Values for 0.1° observation angle are supplementary requirements that shall apply only when specified by the purchaser in the contract or order.

**TABLE 6 7 LuminancType Fac III Sheetor (Y%) (Daytime  
Luminance)g <sup>A</sup>**

Observati Angle	Minimum Angle	White	Yellow	Orange	Green	Red	Blue	Brown
White	—4°	300	200	120	54	54	50	...
0.1° <sup>B</sup>	—4°	300	200	120	54	54	24	14
Yellow	+30°	180	120	72	32	32	30	—45
0.1° <sup>B</sup>	+30°	180	120	72	32	32	14	10
Orange	—4°	250	170	100	45	45	15	—30
0.2°	—4°	250	170	100	45	45	20	12
Green	+30°	150	100	60	25	25	11	8.5
0.2°	+30°	150	100	60	25	25	11	8.5
Red	4.0	—95	—62	—30	15	15	7.5	5.0
0.5°	—4°	—95	—62	—30	15	15	7.5	5.0
Brown	+30°	—65	—45	—25	10	10	5.0	3.5
0.5°	+30°	—65	—45	—25	10	10	5.0	3.5

<sup>A</sup>(Typ Mically Nnimum Coefficien-Mt of Retaroreflized-Mction ( $R_A$ )  $cd/ft^2(cd \cdot lx^{-1} \cdot m^{-2})$ .

<sup>B</sup>Values for 0.1° observatie-Mon atngle are supplementary requirements that shal)Fl apply or-Snly when spetcing T-fied by the purchase-IVr in the contract or order.

6.4 Accelerated Outdoor Weathering Requirements—The retroreflective sheeting shall be weather resistant and show no appreciable cracking, scaling, pitting, blistering, edge lifting, or curling, or more than 1/32-in. (0.8-mm) shrinkage or expansion when tested in accordance with 7.6. Conduct retroreflectivity measurements after outdoor weathering at 0.2° observation and —4° and +30° entrance angles. The minimum coefficient of retroreflection ( $R_A$ ) after weathering is specified in Table 4 5.

NOTE 12—Supplementary Requirement S3, S3 describes a method for artificial accelerated weathering which users of this specification may employ for preliminary judgment until outdoor weathering results are available.

6.5 Colorfastness— After the specified outdoor weathering, the specimen shall conform to the requirements of Table 10 13 and one of the following: Table 2, 5, Table 6, 9, or Table 8 11 when tested in accordance with 7.4 and 7.7.

**TABLE 7 8 Type IV Sheeting<sup>A</sup>**

Observation Angle	Entrance Angle	White	Yellow	Orange	Green	Red	Blue	Brown
<del>0.1<sup>oB</sup></del>	<del>-4<sup>o</sup></del>	<del>2000</del>	<del>1300</del>	<del>800</del>	<del>360</del>	<del>360</del>	<del>32</del>	<del>160</del>
0.1 <sup>oB</sup>	-4 <sup>o</sup>	400	270	160	56	56	32	12
<del>0.1<sup>oB</sup></del>	<del>+30<sup>o</sup></del>	<del>1100</del>	<del>740</del>	<del>440</del>	<del>200</del>	<del>200</del>	<del>7</del>	<del>3.0</del>
0.1 <sup>oB</sup>	+30 <sup>o</sup>	120	740	48	13	13	7	3.0
<del>0.2<sup>o</sup></del>	<del>-4<sup>o</sup></del>	<del>700</del>	<del>470</del>	<del>280</del>	<del>120</del>	<del>120</del>	<del>56</del>	<del>20</del>
0.2 <sup>o</sup>	-4 <sup>o</sup>	250	170	100	35	35	20	7.0
<del>0.2<sup>o</sup></del>	<del>+30<sup>o</sup></del>	<del>400</del>	<del>270</del>	<del>160</del>	<del>72</del>	<del>72</del>	<del>3</del>	<del>5.0</del>
0.2 <sup>o</sup>	+30 <sup>o</sup>	400	270	34	72	72	5.0	2.0
<del>0.5<sup>o</sup></del>	<del>-4<sup>o</sup></del>	<del>160</del>	<del>110</del>	<del>64</del>	<del>28</del>	<del>28</del>	<del>130</del>	<del>4.0</del>
0.5 <sup>o</sup>	-4 <sup>o</sup>	135	100	64	17	17	10	4.0
<del>0.5<sup>o</sup></del>	<del>+30<sup>o</sup></del>	<del>75</del>	<del>51</del>	<del>30</del>	<del>13</del>	<del>13</del>	<del>6</del>	<del>0.05</del>
0.5 <sup>o</sup>	+30 <sup>o</sup>	75	51	30	13	13	3.5	1.4

<sup>A</sup> Minimum Coefficient of Retroreflection ( $R_A$ )  $\text{cd}/\text{ft}^2(\text{cd}\cdot\text{lx}^{-1}\cdot\text{m}^{-2})$ .

<sup>B</sup> Values for 0.1° observation angle are supplementary requirements that shall apply only when specified by the purchaser in the contract or order.

**TABLE 8 9 Daytime Luminance Factor (Y %) (Daytime Luminance)<sup>A</sup>**

Color	Minimum	Maximum
White	45	...
White	40	...
Yellow	42	30
Yellow	24	45
Orange	7.0	25
Orange	12	30
Green	2.5	44
Green	3.0	12
Red	2.5	44
Red	3.0	15
Blue	1.0	10
Brown	4.0	9.0
Brown	1.0	6.0

<sup>A</sup> (Typically Non-Metalized Microprismatic-Delineator Material) For Sheeting Types IV, VII, VIII, and IX.

**TABLE 9 10 Type VI Sheeting<sup>A</sup>**

Observation Angle	Entrance Angle	White	Yellow	Orange	Green	Red	Blue
<del>0.1<sup>oB</sup></del>	<del>-4<sup>o</sup></del>	<del>400</del>	<del>280</del>	<del>100</del>	<del>72</del>	<del>80</del>	<del>40</del>
0.1 <sup>oB</sup>	-4 <sup>o</sup>	2000	1300	800	360	360	160
<del>0.1<sup>oB</sup></del>	<del>+30<sup>o</sup></del>	<del>110</del>	<del>77</del>	<del>26</del>	<del>20</del>	<del>22</del>	<del>14</del>
0.1 <sup>oB</sup>	+30 <sup>o</sup>	1100	77	440	200	200	88
<del>0.2<sup>o</sup></del>	<del>-4<sup>o</sup></del>	<del>250</del>	<del>170</del>	<del>70</del>	<del>30</del>	<del>35</del>	<del>20</del>
0.2 <sup>o</sup>	-4 <sup>o</sup>	700	470	280	120	120	56
<del>0.2<sup>o</sup></del>	<del>+30<sup>o</sup></del>	<del>95</del>	<del>64</del>	<del>26</del>	<del>11</del>	<del>13</del>	<del>7.6</del>
0.2 <sup>o</sup>	+30 <sup>o</sup>	95	64	160	72	72	32
<del>0.5<sup>o</sup></del>	<del>-4<sup>o</sup></del>	<del>200</del>	<del>136</del>	<del>56</del>	<del>24</del>	<del>28</del>	<del>18</del>
0.5 <sup>o</sup>	-4 <sup>o</sup>	160	110	56	28	28	13
<del>0.5<sup>o</sup></del>	<del>+30<sup>o</sup></del>	<del>60</del>	<del>40</del>	<del>17</del>	<del>7.2</del>	<del>8.4</del>	<del>4.8</del>
0.5 <sup>o</sup>	+30 <sup>o</sup>	60	40	17	7.2	8.4	6.0

<sup>A</sup> Minimum Coefficient of Retroreflection ( $R_A$ )  $\text{cd}/\text{ft}^2(\text{cd}\cdot\text{lx}^{-1}\cdot\text{m}^{-2})$ .

<sup>B</sup> Values for 0.1° observation angle are supplementary requirements that shall apply only when specified by the purchaser in the contract or order.

6.6 *Shrinkage*—The retroreflective sheeting shall not shrink in any dimension more than 1/32 in. (0.8 mm) in 10 min or more than 1/8 in. (3.2 mm) in 24 h when tested in accordance with 7.8.

6.7 *Flexibility*—The sheeting shall be sufficiently flexible to show no cracking when tested in accordance with 7.9.

6.8 *Liner Removal*—The liner, when provided, shall be easily removed without soaking in water or other solutions, and shall not break, tear, or remove adhesive from the sheeting. (See 7.10.)

6.9 *Adhesion*—When tested in accordance with 7.5, the adhesive backing of the retroreflective sheeting shall produce a bond that will support a 1 3/4-lb (0.79-kg) weight for adhesive classes 1, 2 and 3 or a 1-lb (0.45-kg) weight for adhesive class 4 for 5 min, without the bond peeling for a distance of more than 2 in. (51 mm).

6.10 *Impact Resistance*—Retroreflective sheeting shall show no cracking or delamination outside of the actual area of impact when subjected to the impact test in accordance with 7.11.

6.11 *Specular Gloss*—The retroreflective sheeting shall have a specular gloss of not less than 40 when tested as specified in 7.12.

TABLE 101 Color Specific Daytime Limits (Daytime Factor) (Y %)<sup>A</sup>

Color	y	xy	x	y	x	y
Color	Minimum	Maxy	x	y	x	y
White	-0.303	-0.300	0.368	0.366	0.340	0.393 0.2740.329
White	15	.300	0.368	0.366	0.340	0.393 0.2740.329
Yellow	-0.498	0.412	0.557	0.442	0.479	0.520 0.4380.472
Yellow	12	0.412	0.557	0.442	0.479	0.520 0.438 0
Orange	-0.558	-0.3520.6360.364	0.570	0.429	0.506	0.404
Orange	7.0	0.636	0.364	0.570	0.429	0.506 0.404
Green <sup>B</sup>	-0.026	0.399	0.166	0.364	0.286	0.446 0.2070.771
Green	2.5	0.399	0.166	0.364	0.286	0.446 0.2070.771
Red	-0.648	-0.3510.7350.265	0.629	0.2810.565	0.346	
Red	2.5	0.735	0.265	0.629	0.2810.565	0.346
Blue <sup>B</sup>	-0.140	0.035	0.2440.2100.190	0.255	0.065	0.216
Blue	1.0	0.035	0.2440.2100.190	0.255	0.065	0.216
Brown	-0.430	0.340	0.6100.390	0.550	0.450	0.4300.390
Brown	1.0	0.340	0.6100.390	0.550	0.450	0.4300.390

<sup>A</sup> (The four pairs of chromaticity coordinates determine the acceptable color in terms of the CIE 1931 Standard Colorimetric System measured with CIE Standard Illuminant D65.

<sup>B</sup> (The saturation limit of green and blue may extend to the border of the CIE chromaticity locus for spectral colors.)

7. Test Methods

7.1 Test Conditions— Unless otherwise specified herein, condition all adhesively bonded and unbonded test samples and specimens at a temperature of 73 ± 3°F (23 ± 2°C) and 50 ± 5 % relative humidity for 24 h prior to testing.

7.2 Panel Preparations—Unless otherwise specified herein, when tests are to be performed using test panels, apply the specimens of retroreflective material to smooth aluminum cut from Alloy 6061-T6 or 5052-H38, in accordance with Specification B 209. The sheets shall be 0.020 in. (0.508 mm), 0.040 in. (1.016 mm) or 0.063 in. (1.600 mm) in thickness, and a minimum of 8 by 8 in. (200 mm by 200 mm). Prepare the aluminum in accordance with Practice Specification B 449, Class 2, or degrease and lightly acid etch before the specimens are applied. Apply the specimens to the panels in accordance with the recommendations of the retroreflective sheeting manufacturer.

7.3 Coefficient of Retroreflection—Determine the coefficients of retroreflection in accordance with Test Method E 810.

7.4 Color—Test for Daytime Color:

7.4.1 Determine the chromaticity and luminance factor Y (%) in accordance with Practice E 308, Test Methods E 308, E 1347, E 1347 and E 1349, and Practices E 991 and E 1164.

7.4.2 For rotationally non-symmetrical materials, make a series of eight measurements. After each of these measurements, rotate the specimen 45° in the same direction about the axis, normal to the specimen surface and average the data. Make additional measurements until such further measurements do not result in a change in the Y value in excess of 1 % of the average to that point.

7.4.3 Instruments (spectrophotometers, colorimeters) used to measure daytime color should have 45/0 or 0/45 illumination and viewing geometry. The illumination angle should not vary from 45° by more than ±10° and the viewing angle should not vary from 0° by more than ±15°, for the 45/0 condition. For the 0/45 condition, the requirements for illumination are interchanged.

7.5 Adhesion—Apply the sheeting to a test panel, 0.040 in. (1.016 mm) minimum thickness, prepared as specified in 7.2. Bond 4 in. (102 mm) of a 1 by 6 in. (25.4 by 152 mm) specimen to a test panel. Condition (see 7.1) and then attach the weight to the free end and allow it to hang free at an angle of 90° to the panel surface for 5 min.

7.6 Outdoor Weathering—Conduct outdoor exposures in accordance with Practice G 7. During exposure, test panels shall be open backed and oriented at an angle of 45° from the horizontal and facing the equator in accordance with Practice G 7. Expose two panels per location for the number of months specified in Table H-14. Conduct exposures in locations with the climate types shown in Table H-15. Panel labeling, and conditioning and handling of panels prior to exposure and during evaluation periods shall be in accordance with Practice G 147.

7.6.1 Specimen Mounting for Type VI Sheetings—Clamp the ends of 100 by 300-mm specimens between 25 by 200 by 2-mm 6061T6 aluminum bars and attach these bars to mounting strips on the outdoor exposure rack. Expose the specimens so that the long axis is parallel to the ground so that bolts used to clamp specimen ends do not interfere with attachment to the rest rack. Fig. 1 is a diagram showing the arrangement of the clamping bars and the test specimen.

7.6.2 Washing Panels after Exposure—Following exposure, gently wash the panels using a soft cloth or sponge and clean water or a dilute solution (1 % by weight in water, maximum concentration) of a mild detergent. After washing, rinse thoroughly with clean water, and blot dry with a soft clean cloth. After washing and drying, condition the panels at room temperature for at least 2 h prior to conducting any property measurements.

7.6.3 Measurement of Coefficient of Retroreflection—After panels have been washed, dried, and conditioned in accordance with 7.6.2, measure retroreflectance at 0.2° observation and -4° and 30° entrance angle. Report the average of the coefficient of retroreflection measured at each geometry on the two panels from each exposure location. Note 2—The HCl solution is used to

**TABLE 12 Climate Types for Use in Outdoor Exposures of Retroreflective VI Sheetings<sup>A</sup>**

Observation Monthly Temperature, °C	Entrance Angle	White	Yellow	Orange	Green	Red	Blue
Climate Type <sup>A</sup>	-4°	400	280	400	72	80	40
0.1° <sup>B</sup>	-4°	400	280	100	72	80	40
0.1° <sup>B</sup>	Warmest Month	Coldest Representative Month Example of a Typical Location					
0.1° <sup>B</sup>	+ 30°	Warmest Representative Month Example of a Typical Location					
77	Tropical summer rain	28 to 34	18 to 22	Miami, FL			
77	Desert	20 to 26	22 to 26	Phoenix, AZ	30	35	20
0.2° (optional; but not recommended)	- 4°	250	170	70	30	35	20
0.2°	+ 30°	95	64	26	11	13	7.6
0.5°	-4°	200	136	56	24	28	18
0.5°	+ 30°	60	40	17	7.2	8.4	4.8

<sup>A</sup> Minimum Coefficient of Reflection (R<sub>fc</sub>) in accordance with the Kropfenreife classification system (R<sub>fc</sub>) cd/lc/Item.

<sup>B</sup> Outdoor exposure results from Miami, FL and Phoenix, AZ are recognized internationally as benchmarks for evaluating durability of many different types of material and products.

<sup>C</sup> Values for exp 0.1° exposures of retroreflective angle are supplementary materials are re-conducted in locations representative of several different climates only when specified by the National Transportation Products Evaluation Program (NTPPEP) under contract to AASHTO.

**TABLE 13 Color Specification Limits (Daytime)<sup>A</sup>**

Color	1		2		3		4	
	x	y	x	y	x	y	x	y
White	0.303	0.300	0.368	0.366	0.340	0.393	0.274	0.329
Yellow	0.498	0.412	0.557	0.442	0.479	0.520	0.438	0.472
Orange	0.558	0.352	0.636	0.364	0.570	0.429	0.506	0.404
Green <sup>B</sup>	0.026	0.399	0.166	0.364	0.286	0.446	0.207	0.771
Red	0.648	0.351	0.735	0.265	0.629	0.281	0.565	0.346
Blue <sup>B</sup>	0.140	0.035	0.244	0.210	0.190	0.255	0.065	0.216
Brown	0.430	0.340	0.610	0.390	0.550	0.450	0.430	0.390

<sup>A</sup> The four pairs of chromaticity coordinates determine the acceptable color in terms of the CIE 1931 Standard Colorimetric System measured with CIE Standard Illuminant D65.

<sup>B</sup> The saturation limit of green and blue may extend to the border of the CIE chromaticity locus for spectral colors.

remove water spots. If the proper water purity (0.2 ppm silica maximum) is used, the colloidal silica deposits that cannot be removed with HCL should be eliminated.

7.7 *Colorfastness*— Use one of the outdoor weathered specimens to test for colorfastness. Wash, dry, and condition panels in accordance with 7.6.2 and test as specified in 7.4.

7.8 *Shrinkage*—Condition a 9 by 9 in. (229 by 229 mm) retroreflective sheeting specimen with liner, a minimum of one h at standard test conditions (see 7.1). Remove the liner and place the specimen on a flat surface with the adhesive side up. Ten min after the liner is removed and again after 24 h, measure the specimen to determine the amount of dimensional change.

**TABLE 14 Outdoor Weathering Photometric Requirements for All Climates**


Type	Months <sup>A</sup>	Minimum Coefficient of Retroreflection, $R_A$
I	24 <sup>B</sup>	50 % of Table 4
II	36 <sup>B</sup>	65 % of Table 6
III	36 <sup>B</sup>	80 % of Table 7
IV	36 <sup>B</sup>	80 % of Table 8
V	36 <sup>B</sup>	80 % of Table 10
VI	6	50 % of Table 12
VII	36 <sup>B</sup>	80 % of Table 1
VIII	36 <sup>B</sup>	80 % of Table 2
IX	36 <sup>B</sup>	80 % of Table 3

<sup>A</sup> Testing at shorter intervals may be done to gather additional information.  
<sup>B</sup> When the colors orange, yellow, or white are specified for construction work zone applications, the outdoor weathering time will be 12 months.

**TABLE 15 Climate Types for Use in Outdoor Exposures of Retroreflective Sheatings**

Climate Type <sup>A,B</sup>	Mean Monthly Temperature, °C		Representative Example of a Typical Location
	Warmest Month	Coldest Month	
Tropical summer rain	28 to 34	18 to 22	Miami, FL
Desert (optional, but recommended) Climate mutually agreed upon between the purchaser and the seller <sup>C</sup>	28 to 34	10 to 17	Phoenix, AZ

<sup>A</sup> Climate classification is in accordance with the Koppen reformed classification system.  
<sup>B</sup> Outdoor exposure results from Miami, FL and Phoenix, AZ are recognized internationally as benchmarks for evaluating durability of many different types of material and products.  
<sup>C</sup> Outdoor exposures of retroreflective sheeting materials are conducted in locations representative of several different climates by the National Transportation Product Evaluation Program (NTPEP) run by AASHTO.

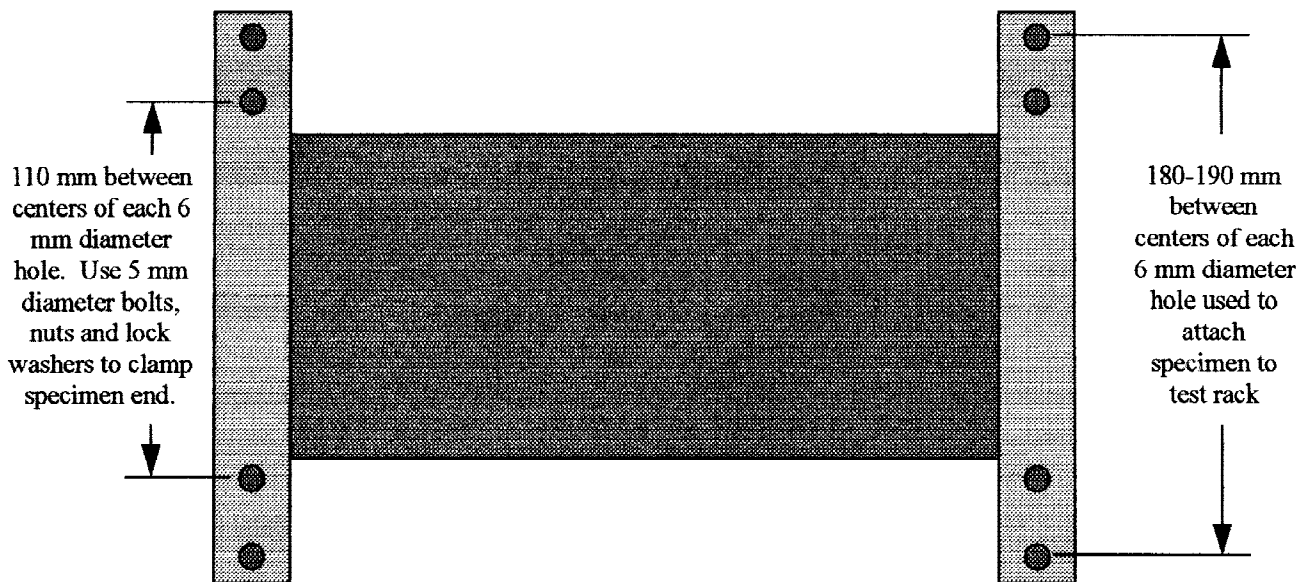

**FIG. 1 Diagram Showing Clamping Bars Used for Attaching Type VI Sheeting Specimens to Test Rack for Outdoor Exposure**

7.9 *Flexibility*— Bend the sheeting, in 1 s, around a 1/8-in. (3.2-mm) mandrel with adhesive contacting the mandrel. For ease of testing, spread talcum powder on the adhesive to prevent sticking to the mandrel. The test specimen shall be 3/4 by 11 in. (70 by 229 mm). The test temperature shall be 73 ± 3°F (23 ± 2°C).

7.10 *Liner Removal*—The protective liner if any, shall be easily removed following accelerated storage for 4 h at 160°F (71°C) under a weight of 2.5 psi (17.2 kPa).

7.11 *Impact Resistance*—Apply the retroreflective sheeting to a 3 by 5 by 0.040 in. (76 by 127 by 1.016 mm) 6061-T6 aluminum test panel as specified in 7.2 and test condition as specified in 7.1. Subject the sheeting to the impact of a 2-lb (0.91-kg) weight, with a 5/8-in. (15.8-mm) diameter rounded tip, dropped from the height necessary to generate an impact of 10 in.-lb (1.13 N-m).

7.12 *Specular Gloss*—Determine the specular gloss of the retroreflective sheeting in accordance with Test Method D 523 at an angle of 85°.

## 8. General Requirements

8.1 *Sheets*—When the retroreflective material is in sheet form, the design, dimension, and tolerances shall be as specified by the purchaser.

8.2 *Rolls*—When ordered in rolls, the retroreflective material shall be evenly wound on a core of sufficient rigidity to prevent distortion of the roll. The maximum number of splices shall be 4/50-yd (46-m) roll. Each splice shall be visible at the edge of the roll. The length and width will be specified by the purchaser.

8.3 *Color Processing*—The sheeting shall permit color processing with compatible transparent and opaque process colors in accordance with the sheeting manufacturer’s recommendation at temperatures between 60 to 100°F (16 to 38°C) and relative humidity at 20 to 80 %.

## 9. Precision and Bias

9.1 The precision and bias for the test methods in Section 7 have not been determined.

## 10. Packaging and Package Marking

10.1 The sheets or rolls manufactured under this specification shall be packaged in accordance with commercially acceptable standards. Each package shall be marked with the following:

Name, Brand or Trademarks	Lot or Run Number
Quantity	Part Number
Size	

## 11. Keywords

11.1 barricades; delineators; highway signing; reboundable sheeting; retroreflective sheeting; traffic control

## SUPPLEMENTARY REQUIREMENTS

The following supplementary requirements shall apply only when specified by the purchaser in the contract or order.

### S1. Fungus Resistance

S1.1 *Scope*—This supplementary specification covers fungus resistance testing.

S1.2 *Test Requirements and Test Methods:*

S1.2.1 *Test Conditions*—Unless otherwise specified herein, all adhesively bonded and unbonded test samples and specimens shall be conditioned at a temperature of 73 ± 3°F (23 ± 2°C) and 50 ± 5 % relative humidity for 24 h prior to testing.

S1.2.2 *Panel Preparations*—Unless otherwise specified herein, when tests are to be performed using test panels, the specimens of retroreflective material shall be applied to smooth aluminum cut from Alloy 6061-T6, in accordance with Specification B 209, sheets in 0.020 in. (0.508 mm) thickness. The aluminum shall be prepared in accordance with ~~Practice Specification~~ B 449, Class 2 or degreased and lightly acid etched before the specimens are applied. The specimens shall be applied to the panels in accordance with the recommendations of the retroreflective sheeting manufacturer.

S1.3 *Fungus Resistance:*

S1.3.1 For use in areas where fungus growth on retroreflective sheeting may be a problem, fungus resistance shall be determined as specified herein.

S1.3.2 After inoculation with the test organism, *Aspergillus niger*, and incubation for 14 days, the retroreflective material shall show no appreciable formation of fungus growth. Any formation of fungus growth shall be noninjurious to the retroreflective material and shall be removable by wiping with a soft cloth.

S1.3.3 *Test Organism*—The test organism used in this test shall be *Aspergillus niger*, ATCC Number 6275.<sup>9</sup> Cultures of this

<sup>9</sup> Available from the American Type Culture Collection (ATCC), 12301 Parklawn Dr., Rockville, MD 20852, or Mycology Laboratory, PRL, U.S. Army Natick Laboratories, Natick, MA 01760.

organism shall be carefully maintained on a potato-dextrose agar medium and promptly renewed if there is evidence of contamination. The stock cultures may be kept for not more than 4 months in a refrigerator at a temperature between  $-7.4 \pm 3$  to  $50^{\circ}\text{F}$  ( $-14 \pm 10^{\circ}\text{C}$  ( $37$  to  $10^{\circ}\text{C}$ ),  $50^{\circ}\text{F}$ ). Subcultures incubated between  $82.4 \pm 28$  to  $86^{\circ}\text{F}$  ( $20 \pm 30^{\circ}\text{C}$  ( $82.4$  to  $30^{\circ}\text{C}$ ),  $86^{\circ}\text{F}$ ) for 10 to 14 days shall be used in preparing the inoculum.

S1.3.4 *Culture Medium*—The culture medium shall have the following composition:

NaNO <sub>3</sub>	3.0 g
<del>K<sub>2</sub>H<sub>2</sub>O<sub>4</sub>PO<sub>4</sub></del>	<del>1.0 g</del>
<del>K<sub>2</sub>HPO<sub>4</sub></del>	<del>1.0 g</del>
MgSO <sub>4</sub> ·7H <sub>2</sub> O	0.5 g
KCl	0.25 g
Agar	15.0 g
Distilled water to make 1000 mL.	

S1.3.5 The pH shall be 5.5 to 6.5: if otherwise, adjust to that range with HCl or NaOH. After mixing, the ingredients shall be sterilized by autoclaving for 15 min at 15 psi (103 kPa) at  $248^{\circ}\text{F}$  ( $120^{\circ}\text{C}$ ). Under sterile conditions, the medium shall be poured into six petri dishes (150 by 20 mm), about 2.2 oz (65 ml) per dish, and allowed to harden.

S1.3.6 *Inoculum*—Add about 0.34 oz (10 ml) of sterile, distilled water containing about 0.005 % of nontoxic wetting agent to a subculture (10 to 14 days old) of the test organism in a ripe, fruiting condition. The spores shall be forced into suspension with a sterile camel's hair brush (or other suitable means) and diluted to 3.4 oz (100 ml) with sterile, distilled water.

S1.3.7 *Preparation of Specimens*—Cut three 3 by 3 in. (76 by 76 mm) specimens from the sample and apply to test panels with the retroreflective surface up. Completely immerse the test specimens in a leaching tank of continuously flowing water for 24 h and then remove and dry. The leaching tank shall be large enough to hold an amount of water weighing not less than 50 times the weight of the specimens. The water entering the tank shall not fall directly on the specimens and shall flow at a rate of 1.3 to 2.6 gal/h (5 to 10 L/h). The pH of the water shall be in the range of 6.0 to 8.0.

S1.3.8 *Inoculation*—Under aseptic conditions, dip each specimen in 70 % ethanol for a few seconds, rinse in distilled water, and place firmly on the surface of the solidified agar medium contained in the petri dishes. Place specimens with the retroreflective surface facing up, one specimen to each dish. With a sterile pipette, distribute 0.03 to 0.05 oz (1.0 to 1.5 ml) of inoculum over the surface of each specimen and the surrounding medium.

S1.3.9 *Incubation Period*—The period of incubation shall be 14 days at a temperature between  $84.2$  to  $89.6^{\circ}\text{F}$  ( $28.9$  to  $32^{\circ}\text{C}$ ) and 85 to 90 % relative humidity.

S1.3.10 *Control*—Test three control specimens of untreated, porous-grade filter paper with the specimens of the retroreflective material to check the viability of the inoculum. At the end of the incubation period, the controls should be covered with fungus growth.

S1.3.11 *Test Results*—Upon completion of the incubation period, examine the specimens visually for fungus growth. Wipe the specimens with a soft cloth wet with a 70 % ethanol solution. Visually examine the specimens for damage resulting from fungus growth. If no pitting or textured surface is found, the sample will be reported to have passed.

## S2. Reboundable Sheeting Requirements

NOTE S2.1—Not all types of sheeting are available in reboundable form.

### S2.1 Performance Requirements:

S2.1.1 *Impact Resistance*—Retroreflective sheeting shall show no cracking or delamination outside of the actual area of impact when subjected to the impact test in accordance with S2.2.1.

S2.1.2 *Flexibility Requirements*—The sheeting shall be sufficiently flexible to show no cracking when tested in accordance with S2.2.2.

S2.1.3 *Adhesion*—When tested in accordance with S2.2.3, the adhesive backing of the retroreflective sheeting shall produce a bond to support a  $1\frac{3}{4}$ -lb (0.79-kg) weight for adhesive classes 1, 2 and 3 or a 1-lb (0.45-kg) weight for adhesive class 4 for 5 min, without the bond peeling for a distance of more than 1 in. (25.4 mm).

S2.1.4 *Outdoor Weathering*—The retroreflective sheeting shall be weather resistant and show no appreciable cracking, scaling, pitting, blistering, edge lifting, or curling, or more than  $\frac{1}{32}$ -in. (0.8-mm) shrinkage or expansion after outdoor exposures specified in 7.6. The outdoor exposure time and minimum coefficient of retroreflection ( $RR_A$ ) after exposure is specified in Table S2.1. Retroreflectivity measurements after outdoor weathering will be made only at  $0.2^{\circ}$  observation and  $-4$  and  $+30^{\circ}$  entrance angles.

### S2.2 Test Method:

S2.2.1 *Impact Resistance*—Retroreflective sheeting, applied to a 3 by 5 by 0.040 in. (76 by 127 by 1.016 mm) 6061-T6 aluminum test panel as specified in 7.2 and test conditioned as specified in 7.1, shall be subjected to the impact of a 4-lb (1.82-kg) weight, with a  $\frac{5}{8}$ -in. (15.8-mm) diameter rounded tip, dropped from the height necessary to generate an impact of 100 in.-lb (11.3 N-m).

S2.2.2 *Flexibility*—The sheeting shall be bent, in one s around a  $\frac{1}{8}$  in. (3.2 mm) mandrel with adhesive contacting the mandrel. For ease of testing, spread talcum powder on the adhesive to prevent sticking to the mandrel. The test specimen shall be  $2\frac{3}{4}$ -inch by 11 inch (70 by 279 mm). The test temperature shall be  $32^{\circ}\text{F}$  ( $0^{\circ}\text{C}$ ).

**TABLE S2.1 Minimum Coefficient of Retroreflection ( $R_A$ ) and Required Outdoor Exposure Times**

Type	Months	Minimum Coefficient of Retroreflection ( $R_A$ )
I	42	65 % of Table 4
II	12	65 % of Table 4
III	42	65 % of Table 3
IV	12	65 % of Table 6
V	42	80 % of Table 4
VI	12	80 % of Table 7
VII	42	80 % of Table 5
VIII	12	80 % of Table 8
IX	42	80 % of Table 7
X	12	80 % of Table 10
XI	6	50 % of Table 9-12
XII	12	50 % of Table 12
XIII	12	80 % of Table 1
XIV	12	80 % of Table 2
XV	12	80 % of Table 3

S2.2.3 *Adhesion*—Apply the sheeting to a test panel, 0.040 in. minimum thickness (1.016 mm), prepared as specified in 7.2. Bond 4 in. of a 1 by 6 in. (25.4 by 152 mm) specimen to a test panel. Condition (see 7.1) and then attach the weight to the free end and allow it to hang free at an angle of 90° to the panel surface for 5 min, without the bond peeling for more than 1 in. (25.4 mm).

S2.2.4 *Outdoor Weathering*—Test two panels in each location in accordance with Table 12.15. After panels have been exposed for the number of months listed in S2.1.4, wash and condition them in accordance with 7.6.2, then test for coefficient of retroreflection. Report the average of the coefficient of retroreflection measured at each geometry on the two panels from each exposure location.

### S3. Artificial Accelerated Weathering

S3.1 *Scope*—This supplementary test may be used for provisional qualification of sheeting before the results from outdoor weathering are available. When they become available, the results from outdoor weathering take precedence over the results from laboratory-accelerated weathering tests.

S3.2 *Test Requirements*—Expose four replicate specimens for the times required in Table S3.1. The minimum length and width for test specimens is 70 mm (2.75 in.). Do not remove panels from the device during a water spray cycle. Make sure they are dry before removing them from the device. After exposure, wash and condition them in accordance with 7.6.2, then measure retroreflectance at 0.2° observation and at -4° and +30° entrance angles. The average retroreflectance of the four replicate specimens shall be at or above the minimum requirements described in Table S3.1. After exposure, the test specimens shall show no appreciable cracking, scaling, pitting, blistering, edge lifting, or curling or more than 1/32-in. (0.8-mm) shrinkage or expansion. The specimens shall also conform to the requirements of Table 10.13 and one of the following: Table 2, 5, Table 6, 9, or Table 8.11 when tested in accordance with 7.4; and 7.7.

S3.3 *Test Conditions*—Conduct exposures in a filtered open flame carbon-arc exposure device conforming to the requirements of Practices G 151 and G 152. The spectral power distribution of the filtered open flame carbon-arc shall conform to the requirements in Practice G 152 for carbon-arc with daylight filters. Use the following exposure cycle:

**TABLE S3.1 Exposure Times and Photometric Requirements for Artificial Accelerated Weathering**

Type	Hours	Minimum Coefficient of Retroreflection ( $R_A$ )
I	1 000	50 % of Table 4
II	1 000	50 % of Table 4
III	2 200 <sup>A</sup>	65 % of Table 3
IV	2 200 <sup>A</sup>	65 % of Table 6
V	2 200 <sup>A</sup>	80 % of Table 4
VI	2 200 <sup>A</sup>	80 % of Table 7
VII	2 200 <sup>A</sup>	80 % of Table 5
VIII	2 200 <sup>A</sup>	80 % of Table 8
IX	2 200	80 % of Table 7
X	2 200	80 % of Table 10
XI	250	50 % of Table 9-12
XII	250	50 % of Table 12
XIII	2 200 <sup>A</sup>	80 % of Table 1
XIV	2 200 <sup>A</sup>	80 % of Table 2
XV	2 200 <sup>A</sup>	80 % of Table 3

<sup>A</sup> When the colors orange, yellow, or white are specified for construction work zone applications, the laboratory-accelerated weathering time will be 500 h.

Continuous light with equilibrium black panel temperature controlled to  $63 \pm 3^\circ\text{C}$  ( $145 \pm 9^\circ\text{F}$ ). Once every 2 h (120 min), spray water on specimens for 18 min.  
 In devices capable of controlling chamber humidity, maintain relative humidity at a  $50 \pm 5\%$  equilibrium during the light-only interval.

## APPENDIXES

### (Nonmandatory Information)

#### X1. Related Information

##### X1.1 Federal Specifications

- X1.1.1 FP85-92 Standard Specifications for Construction of Roads and Bridges on Federal Highways Projects.
- X1.1.2 L-S-300C Federal Specification for Sheeting and Tape, Reflective: Non Exposed Lens.

##### X1.2 Other Specifications

- X1.2.1 American Association of State Highway and Transportation Officials. AASHTO designation ~~M268-84~~ M 268-00 I.

#### X2. Correction Factors for Conversion from Illuminant C to Illuminant D65

X2.1 Table X2.1 lists the correction factors to change measurements made using illuminant C to approximate measurements made using illuminant D65.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*

**TABLE X2.1 Correction Factors for Conversion from Illuminant C to Illuminant D65**

NOTE—As an example, a blue sample which measured (x, y, Y) = (0.150, 0.150, 5.0) using Illuminant C would be converted to (0.149, 0.158, 5.0) to provide the result using Illuminant D65.

Color	x	y	Y
White	+0.003	+0.014	0.00
Yellow	+0.001	+0.002	0.00
Orange	+0.001	+0.001	0.00
Green	+0.000	+0.019	0.00
Red	+0.000	+0.001	0.00
Blue	-0.001	+0.008	0.00
Brown	+0.000	0.000	0.00