



Standard Test Method for Tear-Propagation Resistance of Plastic Film and Thin Sheeting by a Single-Tear Method¹

This standard is issued under the fixed designation D 1938; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of the force necessary to propagate a tear in plastic film and thin sheeting (thickness of 1 mm (0.04 in.) or less) by a single-tear method.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—This standard and ISO 6383-1 are technically equivalent. However, the specimen size is larger for ISO 6383-1.

2. Referenced Documents

2.1 ASTM Standards:

D 374 Test Methods for Thickness of Solid Electrical Insulation²

D 618 Practice for Conditioning Plastics and Electrical Insulating Materials for Testing³

D 882 Test Methods for Tensile Properties of Thin Plastic Sheetings³

D 883 Terminology Relating to Plastics³

D 4000 Classification System for Specifying Plastic Materials⁴

E 4 Practices for Load Verification of Testing Machines⁵

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method⁶

2.2 ISO Standard:

ISO 6383-1 Film and Sheetings—Determination of Tear Resistance Part 1 Trouser Tear Method⁷

3. Terminology

3.1 *Definitions:* Definitions of terms applying to this test method appear in Terminology D 883.

4. Summary of Test Method

4.1 The force to propagate a tear across a film or sheeting specimen is measured using a constant-rate-of-grip separation machine as described in Method A of Test Methods D 882. The force necessary to propagate the tear is interpreted from the load-time chart.

5. Significance and Use

5.1 This test method is of value in rating the tear-propagation force of various plastic films and thin sheeting of comparable thickness. The tear-propagation resistance in highly extensible film or sheeting is distinguished from the tear-propagation resistance in slightly extensible or nonextensible film or sheeting in Fig. 1 and Fig. 2 in 10.1 and 10.2, respectively.

5.2 This test method should be used for specification acceptance testing only after it has been demonstrated that the data for the particular material are acceptably reproducible.

5.3 The data obtained by this test method furnish information for ranking the tear-propagation resistance of plastic films and sheeting of similar composition. Actual use performance may not necessarily correlate with data from this test method. Sets of data from specimens of dissimilar thickness are usually not comparable.

5.4 For many materials, there may be a specification that requires the use of this test method, but with some procedural modifications that take precedence when adhering to the specification. Therefore, it is advisable to refer to that material specification before using this test method. Table 1 of Classification System D 4000 lists the ASTM materials standards that currently exist.

6. Apparatus

6.1 *Film-Testing Machine*, with a force-indicating head that can measure the load applied to tear the specimen. It should be equipped with a device for recording the load carried by the specimen and the amount of separation of the grips during the test. The testing machine shall be essentially free from inertia lag at the specified rate of testing and shall indicate the load

¹ This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.10 on Mechanical Properties. Current edition approved Feb. 15, 1994. Published April 1994. Originally published as D 1938 – 62 T. Last previous edition D 1938 – 93.

² *Annual Book of ASTM Standards*, Vol 10.01.

³ *Annual Book of ASTM Standards*, Vol 08.01.

⁴ *Annual Book of ASTM Standards*, Vol 08.02.

⁵ *Annual Book of ASTM Standards*, Vol 03.01.

⁶ *Annual Book of ASTM Standards*, Vol 14.02.

⁷ Available from American National Standards Institute, 11 W. 42nd St., 13th Floor, New York, NY 10036.

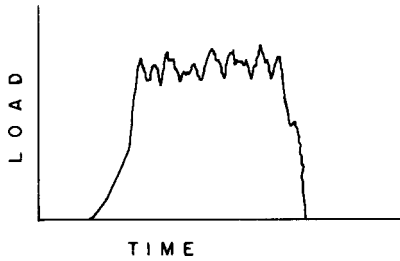


FIG. 1 Load-Time Chart for Low-Extensible Film

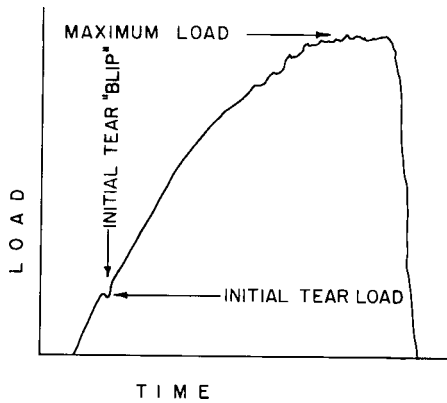


FIG. 2 Load-Time Chart for Highly Extensible Film

with an accuracy of $\pm 2\%$ of the indicated value or better. The accuracy of the testing machine shall be verified in accordance with Practices E 4. A device shall be included to control the grip-separation rate at $250\text{ mm (10 in.)} \pm 5\%/min$.

6.2 *Thickness-Measuring Devices*, in accordance with Test Methods D 374 or a method of equivalent accuracy.

6.3 *Cutter*—A sharp razor blade or the equivalent.

6.4 *Conditioning Apparatus*, in accordance with Procedure A of Practice D 618.

7. Test Specimens

7.1 The specimens shall be of the single-tear type and shall consist of strips 75 mm (3 in.) long by 25 mm (1 in.) wide and shall have a clean longitudinal slit $50\text{ mm (2 in.)} \pm 2\%$ long cut with a sharp razor blade (Fig. 3) or the equivalent.

NOTE 2—The thickness of the test specimens shall be uniform to within 5% of the thickness over the length of the unslit portion of the specimen.

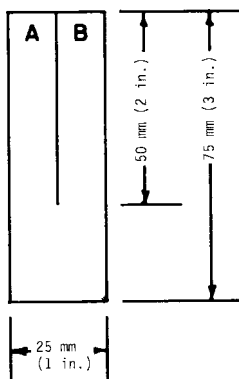


FIG. 3 Single-Tear Specimen

7.2 Measure the thickness of the specimen below the slit (see Fig. 3) in several places and record it in millimetres to the nearest $0.0025\text{ mm (0.0001 in.)}$.

7.3 Cut enough specimens to provide a minimum of five tear-propagation force determinations each in the machine direction and in the transverse direction of the material being tested.

8. Conditioning

8.1 *Conditioning*—Condition the test specimens at $23 \pm 2^\circ\text{C (73.4} \pm 3.6^\circ\text{F)}$ and $50 \pm 5\%$ relative humidity for not less than 40 h prior to test in accordance with Procedure A of Practice D 618, for those tests where conditioning is required. In cases of disagreement, the tolerances shall be $\pm 1^\circ\text{C} (\pm 1.8^\circ\text{F})$ and $\pm 2\%$ relative humidity.

8.2 *Test Conditions*—Conduct tests in the standard laboratory atmosphere of $23 \pm 2^\circ\text{C (73.4} \pm 3.6^\circ\text{F)}$ and $50 \pm 5\%$ relative humidity, unless otherwise specified in the test methods. In cases of disagreement, the tolerances shall be $\pm 1^\circ\text{C} (\pm 1.8^\circ\text{F})$ and $\pm 2\%$ relative humidity.

9. Procedure

9.1 Secure Tongue A (Fig. 3) in one grip and Tongue B in the other grip of the constant-rate-of-grip separation-testing machine, using an initial grip separation of 50 mm (2 in.) . Align the specimen so that its major axis coincides with an imaginary line joining the centers of the grips.

9.2 Using a grip-separation speed of $250\text{ mm (10 in.)/min}$, start the machine, and record the load necessary to propagate the tear through the entire unslit 25-mm (1-in.) portion.

9.3 Test not less than five specimens in each of the principal film or sheeting directions.

10. Calculation

10.1 For thin films and sheeting that have load-time charts characterized by Fig. 1, obtain the average tear propagation force by averaging the load indicated on the chart over the time period, disregarding the initial and final portions of the curve. This can be done with an integrator or a planimeter. In some cases, a fairly accurate estimate can be made by eye.

10.2 For thin films and sheeting that have load-time charts characterized by Fig. 2, obtain and report the initial force to continue the propagation of the slit and the maximum force from the chart. The initial force may be more readily detected by placing a dot approximately $3\text{ mm (} \frac{1}{8}\text{ in.)}$ in a diameter at the base of the razor-blade slit with a china-marking wax pencil. As the load is applied to the sample, observe the dot area. When the load is just sufficient to begin the extension of the slit, introduce a “blip” on the chart (see Fig. 2) by pushing the appropriate button on the recorder or the equivalent to mark this point. The maximum load is the highest reading on the chart. Report both the initial load and the maximum load.

10.3 For each series of tests, report the mean of all values obtained to three significant figures and as the mean value of the particular property.

10.4 Calculate the estimated standard deviation as follows and report to the significant figures:

$$s = \sqrt{(\sum X^2 - n\bar{X}^2)/(n - 1)}$$

where:

- s = estimated standard deviation,
- X = value of a single observation,
- n = number of observations, and
- \bar{X} = arithmetic means of the set of observations.

11. Report

11.1 Report the following information:

11.1.1 Complete identification of the material tested, including type, source, manufacturer’s code number, form, principal dimensions, previous history, orientation of samples with respect to principal directions of the material, etc.,

11.1.2 Average thickness of test specimens,

11.1.3 Number of samples tested,

11.1.4 Date of test, and

11.1.5 Mean of the five average tear-propagation determinations, usually in newtons (or pounds-force), for the materials described in 10.1; and the mean of the five initial tear-propagation forces and the mean of the five maximum tear-propagation forces, usually in newtons (or pounds-force), for materials described in 10.2. In each case, report the standard deviation of the above sets of data. In the cases where the specimens tear to one side, so state, and report the values obtained.

12. Precision and Bias

12.1 Precision:

12.1.1 Table 1 and Table 2 are based on a round robin⁸ conducted between 1986 and 1990 in accordance with Practice E 691 – 87, involving seven materials tested by seven labora-

⁸ Supporting data on precision are available from ASTM Headquarters. Request RR: D20-1177.

TABLE 1 Tear Propagation Resistance (Trouser Tear) Machine Direction (Values Expressed in Units of Grams-Force)

Material	Average	S_r^A	S_R^B	r^C	R^D
Polystyrene	5.04	1.54	3.47	4.32	9.72
Polyester	32.75	7.08	7.08	19.81	19.81
Polypropylene	70.77	20.52	38.05	57.45	106.6
HDPE No. 2	127.3	48.04	56.49	134.59	158.2
LDPE—LD 104	228.3	33.98	33.98	95.14	95.14
LLDPE	337.1	30.95	42.74	86.66	119.7
HDPE No. 1	482.9	49.04	106.0	137.3	296.9

^A S_r = within-laboratory standard deviation for the material stated. It is obtained by pooling the standard deviations of the test results from each laboratory, as follows:

$$S_r = [(\sum(S_1)^2 + (S_2)^2 \dots + (S_n)^2)/n]^{1/2}$$

^B S_R = between-laboratories standard deviation for the material stated. It is a pooling of the amounts by which the average of the test results for each laboratory deviate from the overall average for that material.

^C r = within-laboratory repeatability limit = $2.8 \times S_r$.

^D R = between-laboratories reproducibility limit = $2.8 \times S_R$.

TABLE 2 Tear Propagation Resistance (Trouser Tear) Transverse Direction (Values Expressed in Units of Grams-Force)

Material	Average	S_r^A	S_R^B	r^C	R^D
Polystyrene	3.86	0.46	3.08	1.28	8.63
Polyester	32.47	1.74	3.68	4.86	10.31
LDPE—LD 104	278.6	12.21	30.29	34.18	84.40
Polypropylene	326.2	49.67	124.9	139.1	349.7
LLDPE	372.5	26.69	31.68	74.74	88.70
HDPE No. 2	452.6	24.68	31.28	69.10	87.59
HDPE No. 1	549.7	64.10	105.4	179.5	295.0

^A S_r = within-laboratory standard deviation for the material stated. It is obtained by pooling the standard deviations of the test results from each laboratory, as follows:

$$S_r = [(\sum(S_1)^2 + (S_2)^2 \dots + (S_n)^2)/n]^{1/2}$$

^B S_R = between-laboratories standard deviation for the material stated. It is a pooling of the amounts by which the average of the test results for each laboratory deviate from the overall average for that material.

^C r = within-laboratory repeatability limit = $2.8 \times S_r$.

^D R = between-laboratories reproducibility limit = $2.8 \times S_R$.

tories. For each material, all the samples were prepared at one source, and randomized sections of film were sent to each of the laboratories which prepared the test specimens and tested them. Each test result was the average of five determinations. Each laboratory obtained two test results for each material.

NOTE 3—**Caution:** The following explanations of r and R (12.1.2-12.1.2.3) are intended only to present a meaningful way of considering the approximate precision of this test method. The data in Table 1 and Table 2 should not be rigorously applied to acceptance or rejection of material, as those data are specific to the round robin and may not be representative of other lots, conditions, materials, or laboratories. Users of this test method should apply the principles outlined in Practice E 691 – 87 to generate data specific to their laboratory and materials, or between specific laboratories. The principles of 12.1.2-12.1.2.3 would then be valid for such data.

12.1.2 *Concept of r and R*—If S_r and S_R have been calculated from a large enough body of data and for test results that were the result of testing five specimens, the following applies:

12.1.2.1 *Repeatability Limit, r*—In comparing two test results for the same material obtained by the same operator using the same equipment on the same day, the two test results should be judged not equivalent if they differ by more than the r value for that material.


12.1.2.2 *Reproducibility Limit, R*—In comparing two test results for the same material obtained by different operators using different equipment in different laboratories, the two test results should be judged not equivalent if they differ by more than the R value for that material.

12.1.2.3 Any judgment in accordance with 12.1.2.1 or 12.1.2.2 would have an approximate 95 % (0.95) probability of being correct.

12.2 *Bias*—There are no recognized standards to estimate the bias of this test method.

13. Keywords

13.1 plastic film; single tear; tear; thin sheeting; trouser

 **D 1938**

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.