



Standard Specification for General Requirements for Wrought Copper and Copper- Alloy Plate, Sheet, Strip, and Rolled Bar [Metric]¹

This standard is issued under the fixed designation B 248M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

^{ε1} NOTE—Referenced Documents were corrected editorially in November 2003.

1. Scope

1.1 This specification covers a group of general requirements common to several wrought product specifications. Unless otherwise specified in the purchase order or in an individual specification, these general requirements shall apply to copper and copper-alloy plate, sheet, strip, and rolled bar supplied under each of the following product specifications issued by ASTM: B 36/B 36M, B 96/B 96M, B 103/B 103M, B 121/B 121M, B 122/B 122M, B 152/B 152M, B 169/B 169M, B 194, B 291, B 422, B 465, B 534, B 591, B 592, B 694, B 740, B 747, and B 768.²

NOTE 1—A complete metric companion to Specification B 248 has been developed—B 248M; therefore no metric equivalents are presented in this specification.

2. Referenced Documents

2.1 The following documents of the issue in effect on date of material purchase form a part of this specification to the extent referenced herein:

2.2 ASTM Standards:

- B 36/B 36M Specification for Brass Plate, Sheet, Strip, and Rolled Bar³
- B 96/B 96M Specification for Copper-Silicon Alloy Plate, Sheet, Strip, and Rolled Bar for General Purposes and Pressure Vessels³
- B 103/B 103M Specification for Phosphor Bronze Plate, Sheet, Strip, and Rolled Bar³
- B 121/B 121M Specification for Leaded Brass Plate, Sheet,

- Strip, and Rolled Bar³
- B 122/B 122M Specification for Copper-Nickel-Tin Alloy, Copper-Nickel-Zinc Alloy (Nickel Silver), and Copper-Nickel Alloy Plate, Sheet, Strip, and Rolled Bar³
- B 152/B 152M Specification for Copper Sheet, Strip, Plate, and Rolled Bar³
- B 169/B 169M Specification for Aluminum Bronze Sheet, Strip, and Rolled Bar³
- B 193 Test Method for Resistivity of Electrical Conductor Materials⁴
- B 194 Specification for Copper-Beryllium Alloy Plate, Sheet, Strip, and Rolled Bar³
- B 291 Specification for Copper-Zinc-Manganese Alloy (Manganese Brass) Sheet and Strip⁵
- B 422 Specification for Copper-Aluminum-Silicon-Cobalt Alloy, Copper-Nickel-Silicon-Magnesium Alloy, Copper-Nickel-Silicon Alloy, Copper-Nickel-Aluminum-Magnesium Alloy, and Copper-Nickel-Tin Alloy Sheet and Strip³
- B 465 Specification for Copper-Iron Alloy Plate, Sheet, Strip, and Rolled Bar³
- B 534 Specification for Copper-Cobalt-Beryllium Alloy and Copper-Nickel-Beryllium Alloy Plate, Sheet, Strip, and Rolled Bar³
- B 591 Specification for Copper-Zinc-Tin and Copper-Zinc-Tin-Iron-Nickel Alloys Plate, Sheet, Strip, and Rolled Bar³
- B 592 Specification for Copper-Zinc-Aluminum-Cobalt Alloy, Copper-Zinc-Tin-Iron Alloy Plate, Sheet, Strip, and Rolled Bar³
- B 694 Specification for Copper, Copper-Alloy, and Copper-Clad Stainless Steel (CCS) and Copper-Clad Alloy Steel (CAS) Sheet and Strip for Electrical Cable Shielding³
- B 740 Specification for Copper-Nickel-Tin Spinodal Alloy Strip³

¹ This specification is under the jurisdiction of ASTM Committee B05 on Copper and Copper Alloys, and is the direct responsibility of Subcommittee B05.01 on Plate, Sheet, and Strip.

Current edition approved May 10, 2001. Published September 2001. Originally published as B 248M – 80. Last previous edition B 248M – 96.

² The UNS system for copper and copper alloys (see Practice E 527) is a simple expansion of the former standard designation system accomplished by the addition of a prefix “C” and a suffix “00”. The suffix can be used to accommodate composition variations of the base alloy.

³ *Annual Book of ASTM Standards*, Vol 02.01.

⁴ *Annual Book of ASTM Standards*, Vol 02.03.

⁵ Discontinued. See 1992 *Annual Book of ASTM Standards*, Vol 03.05.

- B 747 Specification for Copper-Zirconium Alloy Sheet and Strip³
- B 768 Specification for Copper-Cobalt-Beryllium Alloy and Copper-Nickel-Beryllium Alloy Strip and Sheet³
- E 8M Test Methods for Tension Testing of Metallic Materials⁶
- E 18 Test Methods for Rockwell Hardness and Rockwell Superficial Hardness of Metallic Materials⁶
- E 29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications⁷
- E 50 Practices for Apparatus, Reagents, and Safety Considerations for Chemical Analysis of Metals, Ores, and Related Materials⁸
- E 53 Test Method for Determination of Copper in Unalloyed Copper by Gravimetry⁸
- E 54 Test Methods for Chemical Analysis of Special Brasses and Bronzes⁸
- E 62 Test Methods for Chemical Analysis of Copper and Copper Alloys (Photometric Method)⁸
- E 75 Test Methods for Chemical Analysis of Copper-Nickel and Copper-Nickel-Zinc Alloys⁸
- E 106 Test Methods for Chemical Analysis of Copper-Beryllium Alloys⁸
- E 112 Test Methods for Determining the Average Grain Size⁶
- E 118 Test Methods for Chemical Analysis of Copper-Chromium Alloys⁸
- E 121 Test Methods for Chemical Analysis of Copper-Tellurium Alloys⁸
- E 255 Practice for Sampling Copper and Copper Alloys for the Determination of Chemical Composition⁸
- E 478 Test Methods for Chemical Analysis of Copper Alloys⁹
- E 527 Practice for Numbering Metals and Alloys (UNS)¹⁰

3. Terminology

3.1 Definitions:

3.1.1 *blank*—a piece of flat product intended for subsequent fabrication by forming, bending, cupping, drawing, or hot pressing, and so forth.

3.1.2 *coil*—a length of the product wound into a series of connected turns. The unqualified term “coil” as applied to “flat product” usually refers to a coil in which the product is spirally wound, with the successive layers on top of one another. (Sometimes called a “roll”.)

3.1.2.1 *level or traverse wound*—a coil in which the turns are positioned into layers parallel to the axis of the coil such that successive turns in a given layer are next to one another.

3.1.2.2 *level or traverse wound on a reel or spool*—a coil in which the turns are positioned into layers on a reel or spool parallel to the axis of the reel or spool such that successive turns in a given layer are next to one another.

3.1.3 *lengths*—straight pieces of the product.

3.1.3.1 *ends*—straight pieces, shorter than the nominal length, left over after cutting the product into mill lengths, stock lengths, or specific lengths. They are subject to minimum length and maximum weight requirements.

3.1.3.2 *mill*—straight lengths, including ends, that can be conveniently manufactured in the mills. Full length pieces are usually 2400, 3000, or 3600 mm and subject to established length tolerances.

3.1.3.3 *multiple*—straight lengths of integral multiples of a base length, with suitable allowance for cutting if and as specified.

3.1.3.4 *specific*—straight lengths that are uniform in length, as specified, and subject to established length tolerances.

3.1.3.5 *specific with ends*—specific lengths, including ends.

3.1.3.6 *stock*—straight lengths that are mill cut and stored in advance of orders. They are usually 2400, 3000, or 3600 mm and subject to established length tolerances.

3.1.3.7 *stock with ends*—stock lengths, including ends.

3.1.4 *plate*—a wrought flat product over 5 mm thick and over 300 mm wide in straight lengths or coils (rolls).

3.1.5 *reel or spool*—a cylindrical device that has a rim at each end and an axial hole for a shaft or spindle, and on which the product is wound to facilitate handling and shipping.

3.1.6 *rolled bar*—a rolled flat product over 5 mm thick and up to and including 300 mm wide, with sheared, sawed, or machined edges, in straight lengths or coils (rolls).

3.1.7 *sheet*—a rolled flat product up to and including 5 mm thick and over 600 mm wide in straight lengths or coils (rolls).

3.1.8 *strip*—a rolled flat product other than flat wire up to and including 5 mm thick in straight lengths, coils (rolls), or traverse wound on reels or spools:

3.1.8.1 with slit or sheared edges in widths up to 600 mm inclusive, and

3.1.8.2 with finished drawn or rolled edges, in widths over 30 to 300 mm inclusive.

4. Materials and Manufacture

4.1 *Materials*—The material shall be of such quality and purity that the finished product shall have the properties and characteristics prescribed in the applicable product specification listed in Section 1.

4.2 *Manufacture*—The material shall be produced by either hot- or cold-working operations. It shall be finished, unless otherwise specified, by such hot working, cold working, annealing, or heat treatment as may be necessary to meet the properties specified.

4.3 *Edges*—The edges shall be slit, shared, sawed, or rolled edges, as specified. Slit edges shall be furnished unless otherwise specified or agreed between the purchaser and supplier or manufacturer. See 5.6 for edge descriptions and tolerances.

5. Dimensions, Mass, and Permissible Variations

5.1 *General*—For the purpose of determining conformance with the dimensional requirements prescribed in this specification, any measured value outside the specified limiting values for any dimension may be cause for rejection.

NOTE 2—Blank spaces in the tolerance tables indicate either that the

⁶ Annual Book of ASTM Standards, Vol 03.01.

⁷ Annual Book of ASTM Standards, Vol 14.02.

⁸ Annual Book of ASTM Standards, Vol 03.05.

⁹ Annual Book of ASTM Standards, Vol 03.06.

¹⁰ Annual Book of ASTM Standards, Vol 01.01.

material is not available or that no tolerances have been established.

5.2 *Thickness*—The standard method of specifying thickness shall be in decimal fractions of a millimetre. For material 0.50 mm and under in thickness, it is recommended that the nominal thicknesses be stated not closer than the nearest 0.01 mm. A list of preferred thicknesses is shown in Appendix X1. The thickness tolerances shall be those shown in Table 1, Table 2, and Table 3 for the product specification indicated:

5.2.1 Table 1—Thickness tolerances applicable to Specifications B 36/B 36M, B 121/B 121M, B 152/B 152M, B 291, B 465, B 591 (Copper Alloy UNS No. C41100), B 592, and B 747.

5.2.2 Table 2—Thickness tolerances applicable to Specifications B 96/B 96M, B 103/B 103M, B 122/B 122M, B 169/B 169M, B 194, B 422, B 534, B 591, B 740, and B 768 (except Copper Alloy UNS No. C41100).

5.2.3 Table 3—Special thickness tolerances applicable to Copper Alloy UNS No. C72500 when ordered to Specification B 122/B 122M, and to Specifications B 194, B 534, B 740, and B 768 as noted in the table.

5.3 *Width*—The width tolerances shall be those shown in Table 4, Table 5, and Table 6, depending on the type of edge required (see 5.3.1, 5.3.2, and 5.3.3):

5.3.1 Table 4—Width tolerances for slit metal and slit metal with rolled edges.

5.3.2 Table 5—Width tolerances for square-sheared metal.

5.3.3 Table 6—Width tolerances for sawed metal.

5.4 *Length*—The material shall be furnished in coils or straight lengths of plate, sheet, strip, or rolled bar as specified. The length tolerances for straight lengths shall be those shown in Table 7, Table 8, or Table 9, depending on the method of cutting required (see 5.4.1, 5.4.2, and 5.4.3). When ends are

permitted, the length and quantity of the ends shall be in accordance with the schedule in Table 8.

5.4.1 Table 7—Length tolerances for straight lengths.

5.4.2 Table 8—Schedule of minimum length and maximum weight of ends for lengths with ends.

5.4.3 Table 9—Length tolerances for square-sheared metal.

5.4.4 Table 10—Length tolerances for sawed metal.

5.5 *Straightness*—The straightness tolerances which are the maximum edgewise curvature (depth of arc) in any 1800-mm portion of the total length, shall be those shown in Table 11, Table 12, and Table 13 depending on the type of edge required.

5.5.1 Table 11—Straightness tolerances for metal as slit, or as slit and straightened, or as slit and edge-rolled, or metal with drawn edges.

5.5.2 Table 12—Straightness tolerances for square-sheared metal.

5.5.3 Table 13—Straightness tolerances for sawed metal.

5.6 *Edges*—When rolled edges are required, they may be produced by either rolling or drawing to one of the following specified edge contours:

5.6.1 *Square Edges (Square Corners)*—Edges shall have commercially square corners with a permissible maximum radius as prescribed in Table 14.

5.6.2 *Rounded Corners*—Edges shall have rounded corners as shown in Fig. 1 with a radius as prescribed in Table 15.

5.6.3 *Rounded Edges*—Edges shall be rounded as shown in Fig. 2 with a radius as prescribed in Table 16.

5.6.4 *Full-Rounded Edges*—Edges shall be full-rounded as shown in Fig. 3 with a radius as prescribed in Table 17.

5.7 *Weight Tolerances for Hot-Rolled Material*:

TABLE 1 Thickness Tolerances

(Applicable to Specifications B 36/B 36M, B 121/B 121M, B 152/B 152M, B 291, B 465, B 591 (Copper Alloy UNS No. C41100), B 592, and B 747)

Thickness, mm		Thickness Tolerances, Plus and Minus, mm						
Over	Through	Strip			Sheet			
		Up to 200 mm, incl, in Width	Over 200 mm to 300 mm, incl, in Width	Over 300 mm to 600 mm, incl, in Width	Over 600 mm to 700 mm, incl, in Width	Over 700 mm to 900 mm, incl, in Width	Over 900 mm to 1200 mm, incl, in Width	Over 1200 mm to 1600 mm, incl, in Width
0.10	0.10	0.007	0.015
	0.20	0.01	0.02	0.03
0.20	0.30	0.015	0.025	0.035
0.30	0.40	0.02	0.03	0.045	0.06	0.08	0.09	0.10
0.40	0.50	0.025	0.035	0.05	0.06	0.08	0.09	0.11
0.50	0.60	0.03	0.04	0.05	0.08	0.09	0.10	0.12
0.60	0.70	0.035	0.05	0.06	0.08	0.09	0.10	0.12
0.70	1.0	0.045	0.05	0.06	0.09	0.10	0.12	0.15
1.0	1.3	0.05	0.06	0.07	0.10	0.12	0.15	0.17
1.3	2.0	0.06	0.07	0.08	0.12	0.15	0.17	0.20
2.0	3.5	0.07	0.08	0.10	0.15	0.17	0.20	0.25
3.5	5.0	0.08	0.10	0.11	.17	0.20	0.25	0.30
		Rolled Bar			Plate			
5.0	8.0	0.10	0.11	0.12	0.22	0.25	0.30	0.35
8.0	13.0	0.11	0.12	0.15	0.30	0.35	0.40	0.45
13.0	20.0	0.13	0.17	0.22	0.40	0.45	0.50	0.60
20.0	30.0	0.17	0.22	0.27	0.45	0.55	0.60	0.75
30.0	40.0	0.55	0.55	0.55	0.55	0.65	0.75	0.90
40.0	60.0	0.65	0.65	0.65	0.65	0.75	0.90	1.1

TABLE 2 Thickness Tolerances

(Applicable to Specifications B 96/B 96M, B 103/B 103M, B 122/B 122M, B 169/B 169M, B 194, B 422, B 534, B 591, B 740 (except Copper Alloy UNS No. C41100), and B 768)

Thickness, mm		Thickness Tolerances, Plus and Minus, mm							
Over	Through	Strip			Sheet				
		Up to 200 mm, incl, in Width	Over 200 mm to 300 mm, incl, in Width	Over 300 mm to 600 mm, incl, in Width	Over 600 mm to 700 mm, incl, in Width	Over 700 mm to 900 mm, incl, in Width	Over 900 mm to 1200 mm, incl, in Width	Over 1200 mm to 1600 mm, incl, in Width	
0.10	0.10	0.01	0.02	
0.10	0.20	0.015	0.025	0.035	
0.20	0.30	0.02	0.03	0.05	
0.30	0.40	0.025	0.035	0.06	
0.40	0.50	0.03	0.05	0.06	
0.50	0.60	0.035	0.06	0.07	
0.60	0.70	0.05	0.06	0.07	0.10	0.13	0.15	0.18	
0.70	1.0	0.06	0.07	0.08	0.13	0.15	0.18	0.20	
1.0	1.3	0.07	0.08	0.10	0.15	0.18	0.20	0.25	
1.3	2.0	0.08	0.10	0.11	0.18	0.20	0.25	0.30	
2.0	3.5	0.10	0.11	0.12	0.20	0.25	0.30	0.35	
3.5	5.0	0.11	0.13	0.15	0.25	0.30	0.35	0.40	
		Rolled Bar			Plate				
5.0	8.0	0.13	0.15	0.18	0.30	0.35	0.40	0.45	
8.0	13.0	0.15	0.18	0.20	0.40	0.45	0.50	0.60	
13.0	20.0	0.20	0.25	0.30	0.50	0.55	0.60	0.75	
20.0	30.0	0.30	0.40	0.50	0.60	0.65	0.75	0.95	
30.0	40.0	0.70	0.70	0.70	0.70	0.80	0.95	1.2	
40.0	60.0	0.85	0.85	0.85	0.85	0.95	1.1	1.4	

TABLE 3 Special Thickness Tolerances

Thickness, mm	Tolerances Applicable to Copper Alloy UNS No. C72500, Specifications B 122/B 122M and B 740 Tolerances, Plus and Minus, ^A mm for Strip 200 mm and Under in Width	Tolerances Applicable to Specifications B 194, B 534, and B 768 Tolerances, Plus and Minus, ^A mm for Strip 100 mm and Under in Width
	0.10 and under	0.005
Over 0.10 to 0.16, incl	0.008	0.008
Over 0.16 to 0.22, incl	0.010	0.013
Over 0.22 to 0.35, incl	0.013	0.015
Over 0.35 to 0.45, incl	0.018	0.018
Over 0.45 to 0.55, incl	0.020	0.020
Over 0.55 to 0.60, incl	0.025	0.025
Over 0.65 to 0.80, incl	0.033	0.025
Over 0.80 to 1.2, incl	0.038	...

^AIf tolerances are specified as all plus or all minus, double the values given.

5.7.1 *Table 18*—Lot weight tolerances for hot-rolled sheet and plate applicable to Specifications B 96/B 96M (Copper Alloy UNS Nos. C65500 and C65800) and B 152/B 152M.

5.7.2 The weight of each lot of five or more plates or sheets of the same type and the same specified dimensions, when ordered to thickness, shall not vary from the theoretical by more than the amount prescribed in Table 18 for the product specification indicated. The weight of any individual plate or sheet may vary from the nominal by not more than one third in excess of the tolerances prescribed in Table 18 for the product specification indicated. The tolerances for lots of less than five plates or sheets shall be governed by the tolerances for individual plates or sheets.

5.7.3 For the purpose of calculation, the densities of the materials covered by these specifications are listed in Appendix X2.

6. Workmanship, Finish, and Appearance

6.1 The material shall be free of defects, but blemishes of a nature that do not interfere with normal commercial operations are acceptable. It shall be well cleaned and free of dirt. A superficial film of residual light lubricant is normally present and is acceptable unless otherwise specified.

6.2 The surface finish and appearance shall be the normal commercial quality for the alloy, thickness, and temper ordered. When application information is provided with purchase order, the surface shall be that commercially producible for the application. Superficial films of discoloration, or lubricants, or tarnish inhibitors are permissible unless otherwise specified.

7. Sampling

7.1 *Sampling*—The lot size, portion size, and selection of sample pieces shall be as follows:

7.1.1 *Lot Size*—An inspection lot shall be 5000 kg or less material of the same mill form, alloy, temper and nominal dimensions, subject to inspection at one time, or shall be the product of one cast bar from a single melt charge, whose weight shall not exceed 12 000 kg that has been continuously processed and subject to inspection at one time.

7.1.2 *Portion Size*—A portion shall be four or more pieces selected to be representative of each lot. If the lot consists of less than four pieces, representative samples shall be taken from each piece.

7.1.2.1 *Chemical Analysis*—A sample for chemical analysis shall be taken in accordance with Practice E 255 for product in

TABLE 4 Width Tolerances for Slit Metal and Slit Metal with Rolled Edges
(Applicable to all specifications listed in 2.2)

Width, mm	Width Tolerances, ^A Plus and Minus, mm			
	For Thicknesses 0.102 to 0.80 mm, incl	For Thicknesses Over 0.80 to 3.2 mm, incl	For Thicknesses Over 3.2 to 5.0 mm, incl	For Thicknesses Over 5.0 to 12.0 mm, incl
50.8 and under	0.13	0.25	0.30	0.38
Over 50.8 to 200, incl	0.20	0.33	0.38	0.38
Over 200 to 600, incl	0.40	0.40	0.40	0.79
Over 600 to 1020, incl	0.79	0.79	0.79	1.19

^AIf tolerances are specified as all plus or all minus, double the values given.

TABLE 5 Width Tolerances for Square-Sheared Metal
(Applicable to all specifications listed in 2.2)

ASTM Designation

Weight of
Sample,
min, g

NOTE 1—All lengths up to 3.05 m, inclusive.

Width, mm	Width Tolerances, ^A Plus and Minus, mm		
	1.59 mm and Under in Thick- ness	Over 1.5 mm to 3.5 mm, incl, in Thickness	Over 3.5 mm in Thickness
500 and under	0.79	1.2	1.6
Over 500 to 900, incl	1.2	1.2	1.6
Over 900 to 3000, incl	1.6	1.6	1.6

^AIf tolerances are specified as all plus or all minus, double the values given.

B 36/B 36M, B 96/B 96M, B 121/B 121M,
B 122/B 122M, B 152/B 152M, B 169/B 169M, B 194,
B 291, B 422, B 465, B 534, B 591, B 592, and
B 740
B 103/B 103M

150

225

7.1.2.2 Samples for All Other Tests—Samples for all other tests shall be taken from the sample portion in 7.1.2 and be of a convenient size to accommodate the test and comply with the requirements of the appropriate ASTM standard and test methods.

TABLE 6 Width Tolerances for Sawed Metal
(Applicable to all specifications listed in 2.2)

Width, mm	Width Tolerances, ^A Plus and Minus, mm		
	For Lengths Up to 3000 mm, incl	For Length Over 3000 mm	
	For Thick- nesses Up to 38 mm, incl	For Thick- nesses Over 38.1 mm	All Thick- nesses
Up to 300, incl	0.79	1.6	1.6
Over 300 to 3000, incl	1.6	1.6	1.6

^AIf tolerances are specified as all plus or all minus, double the values given.

TABLE 7 Length Tolerances for Straight Lengths
(Applicable to all specifications listed in 2.2 except B 694)

NOTE 1—The following length tolerances are all plus: if all minus tolerances are desired, use the same values; if tolerances are desired plus and minus, halve the values given.

Length, mm	Length Toler- ances, mm
Specific lengths, mill lengths, multiple lengths, and specific lengths with ends	
3000 and under	6.4
Over 3000 to 6000, incl	13
Stock lengths and stock lengths with ends	25 ^A

^AAs stock lengths are cut and placed in stock in advance of orders, departure from this tolerance is not practicable.

its final form. Unless required otherwise by the purchaser at the time the order is placed, the manufacturer shall have the option of determining conformance to chemical composition by analyzing samples taken at the time the castings are poured or samples taken from the semifinished product, if heat identity can be maintained throughout all operations. If the manufacturer determined the chemical composition of the material during the course of manufacture, he shall not be required to sample and analyze the finished product. The minimum weight of the composite sample in accordance with Practice E 255 shall be as follows:

8. Number of Tests and Retests

8.1 Chemical Requirements:

8.1.1 When samples are taken at the time the castings are poured, at least one sample shall be analyzed for each group of castings poured simultaneously from the same source of molten metal.

8.1.2 When samples are taken from the semifinished or finished product, at least one sample representative of the product of each cast bar from a single melt charge continuously processed with heat identity maintained shall be analyzed.

8.1.3 When samples are taken from the semifinished or finished product and heat identity has not been maintained, a single sample representative of each 5000-kg lot, or fraction thereof, shall be analyzed. When the product piece is greater than 5000 kg, one sample to be representative of the product piece shall be analyzed.

8.2 Mechanical and Electrical Requirements and Grain Size—Unless otherwise provided in the product specification, test specimens shall be taken from two of the sample pieces selected in accordance with 7.1.2. The required tests shall be made on each of the specimens so selected. In the case of copper alloy Specifications B 194, B 534, and B 740 two specimens shall be taken from each of two sample pieces selected in accordance with 7.1.2. One specimen from each sample piece shall be tested without further treatment, and the other two specimens shall be tested after precipitation hardening. In the case of the requirements in Table 4, Mill Hardened Tempers, in Specifications B 194 and B 740, only two specimens need to be taken and tested, because the product is in the precipitation hardened temper as supplied. The reported value shall be the arithmetic average of the readings. In the case of hardness, three readings shall be taken and averaged for each sample.

8.3 Retests:

TABLE 8 Schedule of Minimum Length and Maximum Weight of Ends for Mill Lengths, Specific Lengths with Ends, and Stock Lengths with Ends

(Applicable to all specifications listed in 2.2 except B 694)

Nominal Length, mm	1.3 mm and Under in Thickness		Over 1.3 to 3.2 mm, incl, in Thickness		Over 3.2 to 6.5 mm, incl, in Thickness	
	Minimum Length of Shortest Piece, mm	Maximum Permissible Weight of Ends, % of Lot Weight	Minimum Length of Shortest Piece, mm	Maximum Permissible Weight of Ends, % of Lot Weight	Minimum Length of Shortest Piece, mm	Maximum Permissible Weight of Ends, % of Lot Weight
1800 to 2400, incl	1200	20	1200	25	900	30
2400 to 3000, incl	1800	25	1500	30	1200	35
3000 to 4300, incl	2000	30	1800	35	1500	40

TABLE 9 Length Tolerances for Square-Sheared Metal in All Widths 3000 mm and Under

(Applicable to all specifications listed in 2.2 except B 694)

Length, mm	Length Tolerance, ^A Plus and Minus, mm		
	For Thicknesses Up to 1.6 mm, incl	For Thicknesses 1.6 to 3.2 mm, incl	For Thicknesses Over 3.2mm
508 and under	0.8	1.2	1.6
Over 508 to 914, incl	1.2	1.2	1.6
Over 914 to 3048, incl	1.6	1.6	1.6

^AIf tolerances are specified as all plus or all minus, double the values given.

TABLE 10 Length Tolerances for Sawed Metal

(Applicable to all specifications listed in 2.2 except B 694)

NOTE 1—The following tolerances are all plus; if all minus tolerances are desired, use the same values; if tolerances are desired plus and minus, halve the values given.

Width, mm	Length Tolerance, mm
Up to 3000, incl	64

TABLE 11 Straightness Tolerances for Slit Metal or Slit Metal Either Straightened or Edge-Rolled

(Applicable to all specifications listed in 2.2)

Width, mm	Maximum Edgewise Curvature (Depth of Arc) in any 1800-mm Portion of the Total Length		
	Straightness Tolerance, mm		
	As Slit Only	As Slit and Either Straightened or Edge Rolled	
	Shipped in Rolls	Shipped Flat	Shipped Flat, in Rolls, or on Bucks
Over 6 to 10, incl	51	38	13
Over 10 to 12, incl	38	25	13
Over 12 to 25, incl	25	19	13
Over 25 to 50, incl	16	16	9.5
Over 50 to 100, incl	13	13	9.5
Over 100	9.5	9.5	9.5

8.3.1 If the chemical analysis of the specimens prepared from samples selected in accordance with 7.1.2 fails to conform to the specified limits, analysis shall be made on a new composite sample prepared from the pieces selected in accordance with 7.1.2.

8.3.2 If one of the two tests made to determine any of the mechanical or physical properties fails to meet a specified limit, this test shall be repeated on the remaining pieces,

TABLE 12 Straightness Tolerances for Square-Sheared Metal

(Applicable to all specifications listed in 2.2)

(Not applicable to metal over 3000 mm in length)

Thickness, mm	Maximum Edgewise Curvature (Depth of Arc) in any 1800-mm Portion of the Total Length	
	Straightness Tolerances, mm	
	Up to 250 mm, incl, in Width	Over 250 mm in Width
3.2 and under	1.6	0.79
Over 3.2 to 5.0, incl	3.2	1.2
Over 5.0	3.2	1.6

TABLE 13 Straightness Tolerances for Sawed Metal

(Applicable to all specifications listed in 2.2)

(Not applicable to metal over 3600 mm in length)

Width, mm	Maximum Edgewise Curvature (Depth of Arc) in Any 2000-mm Portion of the Total Length	
	Straightness Tolerances, mm	
80 and under	1.6	
Over 80	1.2	

TABLE 14 Tolerances for Radius of Commercially Square Corners of Rolled or Drawn Edges with Square Corners

(Applicable to all specifications listed in 2.2 except B 694)

Thickness, mm	Permissible Radius of Corners, max, mm
0.8 to 1.6, incl	0.25
Over 1.6 to 4.8, incl	0.40
Over 4.8 to 25, incl	0.8


maximum of two, selected in accordance with 7.1.2 and the results of both of these tests shall comply with the specified requirements.

8.3.3 If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

8.3.4 If the percent elongation of any tension test specimen is less than that specified and any part of the fracture is outside the middle two thirds of the gage length or in a punched or scribed mark within the reduced section, a retest shall be allowed.

8.3.5 If a bend test specimen fails, due to conditions of bending more severe than required by the specification, a retest shall be permitted, either on a duplicate specimen or on a remaining portion of the failed specimen.

8.3.6 After removal of defective specimens and correction of test methods, only one retest cycle is permitted. If after the

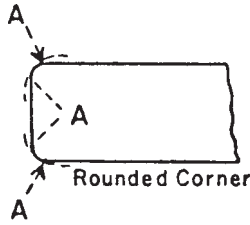


NOTE 1—The arc of the rounded corner shall not necessarily be tangent at points “A,” but the product shall be commercially free from sharp, rough, or projecting edges.

FIG. 1 Rounded Corners

TABLE 15 Tolerances for Radius on Corners of Rolled or Drawn Edges with Rounded Corners
(Applicable to all specifications listed in 2.2 except B 694)

Thickness, mm	Radius of Corners, mm	
	Min	Max
Up to 3.2, incl ^A
Over 3.2 to 4.8, incl	0.40	1.2
Over 4.8 to 25, incl	0.80	2.4
Over 25 to 50, incl	1.6	4.8

^ANot available.

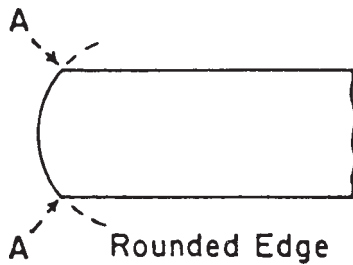

NOTE 1—The arc of the rounded edge shall be substantially symmetrical with the axis of the product. The corners “A” will usually be sharp but shall not have rough or projecting edges.

FIG. 2 Rounded Edge

TABLE 16 Tolerances for Radius of Rolled or Drawn Rounded Edges
(Applicable to all specifications listed in 2.2 except B 694)

Thickness, mm	Radius of Edges ^A	
	Min	Max
Up to 4.78, incl	$\frac{1}{4} t$	$1\frac{3}{4} t$
Over 4.78	$1 t$	$1\frac{1}{2} t$

^AThe t refers to the measured thickness of the test specimen.

retest the material fails to meet the requirements of this specification, it shall be rejected.

9. Specimen Preparation

9.1 *Chemical Analysis*—A composite sample of the semi-finished or finished product shall be prepared in accordance with Practice E 255 or as described in 7.1.2.1.

9.2 Specimens shall be prepared in accordance with the method prescribed in 10.3 for all other tests. Full cross section specimens shall be used whenever possible. Samples shall be representative of the condition of the material, and particular specimen preparation techniques shall be stated in the specific product specification.



Full Rounded Edge

NOTE 1—The arc of the rounded edge shall not necessarily be tangent at points “A” but shall be substantially symmetrical with the axis of the product, and the product shall be commercially free from sharp, rough, or projecting edges.

FIG. 3 Full Rounded Edge

TABLE 17 Tolerances for Radius of Rolled or Drawn Full-Rounded Edges
(Applicable in all specifications listed in 2.2)

Thickness, mm	Radius of Edges ^A	
	Min	Max
All thicknesses	$\frac{1}{2} t$	$\frac{3}{4} t$

10. Test Methods

10.1 The test method used for routine chemical analysis for specification compliance and preparation of certifications and test reports, when required, shall be at the discretion of the reporting laboratory.

10.1.1 Commonly accepted technique for routine chemical analysis of copper and copper alloys include, but are not limited to, X-ray fluorescence spectroscopy, atomic absorption spectrophotometry, argon plasma spectroscopy, and emission spectroscopy.

10.2 In case of disagreement concerning chemical composition, an applicable test method for chemical analysis may be found in Test Methods E 53, or Test Methods E 54, E 62, E 75, E 106, E 118, E 121, or E 478.

10.2.1 The specific test method(s) to be used shall be stated in the particular product specification.

10.2.2 In case of disagreement concerning sulfur content, the test method described in the Annex shall be used.

10.3 The following test methods shall be used for determining the mechanical and physical properties required in the specifications listed in Section 1:

Tension	E 8M
Grain size	E 112
Rockwell hardness	E 18
Electrical resistivity	B 193

10.3.1 The testing procedure used for a particular property is dependent upon alloy, temper, and configuration of the product. The manufacturer shall have the option of selecting the most representative procedure unless a specific procedure is specified at the time the contract is placed.

11. Significance of Numerical Limits

11.1 For the purposes of determining compliance with the specified limits for requirements of the properties listed in the following table, an observed value or a calculated value shall be rounded as indicated in accordance with the rounding method of Practice E 29.

TABLE 18 Lot Weight Tolerances for Hot-Rolled Sheet and Plate

(Applicable to Specifications B 36/B 36M, B 96/B 96M (Copper Alloy UNS Nos. C65500 and C65800), B 103/B 103M, B 122/B 122M, B 152/B 152M, and B 591)

Thickness, mm	Weight Tolerances, Plus and Minus, Percentage of Theoretical Weight				
	1200 mm and Under in Width	Over 1200 to 1500 mm, incl, in Width	Over 1500 to 1800 mm, incl, in Width	Over 1800 to 2200 mm, incl, in Width	Over 2200 to 2800 mm, incl, in Width
3.18 and under	8	9.5	11	12.5	14
Over 3.18 to 4.78, incl	6.5	8	9.5	11	12.5
Over 4.78 to 6.35, incl	6	7.5	8.5	9	10
Over 6.35 to 7.92, incl	5.5	7	8	8.5	9
Over 7.92 to 9.53, incl	5	6	7	7.5	8
Over 9.53 to 11.1, incl	4.5	5	6	7	7.5
Over 11.1 to 12.7, incl	4	4.5	5.5	6	6.5
Over 12.7 to 15.9, incl	3.5	4.5	5	5.5	6
Over 15.9 to 19.1, incl	3	4	4.5	5	5.5
Over 19.1 to 25.4, incl	2.75	3.5	4	4.5	5
Over 25.4 to 38.1, incl	2.5	3	3.5	4	4.5
Over 38.1 to 50.8, incl	2.25	2.75	3.25	3.75	4.25

Property	Rounded Unit for Observed or Calculated Value
Chemical composition	nearest unit in the last righthand significant digit
Hardness	used in expressing the limiting value
Electrical resistivity	
Electrical conductivity	
Tensile strength	nearest 5 MPa
Yield strength	nearest 5 MPa
Elongation:	nearest 1 %
Grain size:	
Under 0.060 mm	nearest multiple of 0.005 mm
0.060 mm and over	nearest 0.01 mm

12. Inspection

12.1 The manufacturer or supplier shall inspect and make tests necessary to verify that the product furnished conforms to the requirements specified.

12.2 Source inspection of the material by the purchaser may be agreed upon between the manufacturer or supplier and the purchaser as part of the purchase contract. In this case, the nature of the facilities needed to satisfy the inspector representing the purchaser that the product is being furnished in accordance with this specification shall be included in the agreement. All tests and the inspection shall be conducted so as not to interfere unnecessarily with the operation of the works.

12.3 The manufacturer or supplier and the purchaser, by mutual agreement, may accomplish the final inspection simultaneously.

13. Rejection and Rehearing

13.1 Material that fails to conform to the requirements of this specification may be rejected. Rejection should be reported to the manufacturer or supplier promptly and in writing. In case of dissatisfaction with the results of the test, the manufacturer or supplier may make claim for rehearing.

14. Certification

14.1 When specified in the purchase order or contract, a manufacturer's certificate of compliance shall be furnished to the purchaser stating that each lot has been sampled, tested, and inspected in accordance with this specification and that the requirements have been met.

15. Mill Test Report

15.1 When specified in the purchase order or contract, the manufacturer or supplier shall furnish to the purchaser a manufacturer's test report showing the results of the required tests.

16. Packaging and Package Marking

16.1 The material shall be separated by size, composition, and temper, and prepared for shipment in such a manner as to ensure acceptance by common carrier for transportation, and to afford protection from the normal hazards of transportation.

16.2 Each shipping unit shall be legibly marked with the purchase order number, metal or alloy designation, temper, size, shape, gross and net weight, and name of supplier. The specification number shall be shown, when specified.

16.3 *Product Identification*—For *ASME Boiler and Pressure Vessel Code* applications, the name or trademark of the manufacturer and the manufacturer's lot identification number shall be legibly stamped or stenciled on each finished plate and sheet in two places not less than 300 mm from the edges. If the plate and sheet are too small to locate the markings as above, the marking may be placed near the center of the plate and sheet. In the case of butt straps, the markings may be placed 300 mm from the end. The plate number and type shall be legibly stamped on each plate and on each test specimen.

17. Keywords

17.1 general requirements, plate; general requirements, rolled bar; general requirements, sheet; general requirements, strip; general requirements, wrought copper and copper alloys

SUPPLEMENTARY REQUIREMENTS

The following supplementary requirements shall apply only when specified by the purchaser in the inquiry, contract, or order, for agencies of the U.S. government.

S1. Referenced Documents

S1.1 The following documents of the issue in effect on date of material purchase form a part of this specification to the extent referenced herein:

S1.1.1 *Federal Standards*:¹¹

Fed. Std. No. 102 Preservation, Packaging and Packing Levels

Fed. Std. No. 123 Marking for Shipment (Civil Agencies)

Fed. Std. No. 185 Identification Marking of Copper and Copper-Base Alloy Mill Products

S1.1.2 *Military Standards*:¹¹

MIL-STD-129 Marking for Shipment and Storage

MIL-C-3993 Packaging of Copper and Copper-Base Alloy Mill Products

S2. Quality Assurance

S2.1 *Responsibility for Inspection*:

S2.1.1 Unless otherwise specified in the contract or purchase order, the manufacturer is responsible for the performance of all inspection and test requirements specified. Except as otherwise specified in the contract or purchase order, the manufacturer may use his own or any other suitable facilities for the performance of the inspection and test requirements unless disapproved by the purchaser at the time the order is

placed. The purchaser shall have the right to perform any of the inspections and tests set forth when such inspections and tests are deemed necessary to assure that the material conforms to prescribed requirements.

S3. Identification Marking

S3.1 All material shall be properly marked for identification in accordance with Fed. Std. No. 185 except that the ASTM specification number and the alloy number shall be used.

S4. Preparation for Delivery

S4.1 *Preservation, Packaging, Packing*:

S4.1.1 *Military Agencies*—The material shall be separated by size, composition, grade or class and shall be preserved and packaged, Level A or C, packed, Level A, B, or C, as specified in the contract or purchase order, in accordance with the requirements of MIL-C-3993.

S4.1.2 *Civil Agencies*—The requirements of Fed. Std. No. 102 shall be referenced for definitions of the various levels of packaging protection.

S4.2 *Marking*:

S4.2.1 *Military Agencies*—In addition to any special marking required by the contract or purchase order, marking for shipment shall be in accordance with MIL-STD-129.

S4.2.2 *Civil Agencies*—In addition to any special marking required by the contract or purchase order, marking for shipment shall be in accordance with Fed. Std. No. 123.

¹¹ Available from Standardization Documents Order Desk, Bldg. 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094.

ANNEX**(Mandatory Information)****A1. TEST METHOD FOR SULFUR BY COMBUSTION AND INFRARED DETECTOR****A1.1 Scope**

A1.1.1 This test method covers the determination of sulfur in electrolytic cathode copper.

A1.1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

A1.2 Summary of Test Method

A1.2.1 The sulfur is converted to sulfur dioxide (SO₂) by combustion in a stream of oxygen and the SO₂ is measured by infrared absorption.

A1.2.2 This test method is written for use with commercial analyzers equipped to carry out the above operations automatically.

A1.3 Interferences

A1.3.1 The elements ordinarily present do not interfere.

A1.4 Apparatus

A1.4.1 *Combustion and Analyzing Instrumentation*, capable of making the required measurements.

A1.5 Reagents and Materials

A1.5.1 *Reagents*:

A1.5.1.1 *Accelerator*—Use the accelerator recommended by the instrument manufacturer which, for copper, should be sulfur and tin free.

A1.5.1.2 *Oxygen*—Ultra high purity, 99.95 % min. Other grades of oxygen may be used if sulfur free, or the oxygen may be purified as described in Practices E 50.

A1.5.2 *Materials*:

A1.5.2.1 *Crucibles*—Use crucibles recommended by the manufacturer, or equivalent.

A1.5.2.2 *Crucible Tongs*—Use tongs capable of handling recommended crucibles.

A1.6 Hazards

A1.6.1 For precautions to be observed in the use of certain reagents in this test method, refer to Practice E 50.

A1.6.2 Use care when handling hot crucibles and operating the furnace to avoid burns and electrical shock.

A1.7 Preparation of Apparatus

A1.7.1 Assemble and test the apparatus according to the manufacturer's instructions.

A1.8 Sample Preparation

A1.8.1 The sample should be uniform in size but not finer than 40 mesh.

A1.9 Calibration

A1.9.1 *Calibration Reference Materials*—Select a minimum of two reference materials with sulfur content near the mid-point and high limit.

A1.9.2 *Instrument Calibration*—Calibrate according to the manufacturer's instructions.

A1.10 Procedure

A1.10.1 Stabilize the furnace and analyzer according to the manufacturer's instruction.

A1.10.2 Transfer the weight of sample recommended by the manufacturer into a crucible and add the same amount of accelerator used in the calibration. Proceed as directed by the manufacturer's instructions.

A1.11 Calculation

A1.11.1 Since most commercially available instruments calculate percent concentrations directly, including corrections for blank and sample weight, calculations by the analyst are not required.

A1.11.2 If the analyzer does not compensate for blank and sample weight values, use the following equation:

$$\text{Sulfur, \%} = \frac{(A - B) \times C}{D} \quad (\text{A1.1})$$

where:

A = Digital Voltmeter (DVM) reading for specimen,

B = DVM reading for blank,

C = weight compensator setting, and

D = specimen weight, g.

A1.12 Precision and Bias

A1.12.1 *Precision*—The precision of this test method is dependent upon sample preparation care and preciseness of calibration.

A1.12.2 *Bias*—The accuracy of this test method is dependent to a large extent upon the accuracy of the methods used to determine the sulfur concentration in the calibration standards as well as their homogeneity.

APPENDIXES

(Nonmandatory Information)

X1. PREFERRED THICKNESSES FOR UNCOATED WROUGHT COPPER AND COPPER ALLOY PLATE, SHEET, STRIP, AND ROLLED BAR, UP TO 6.5 mm INCL

X1.1 It is recommended that wherever possible material purchased to these specifications be ordered in thicknesses listed as follows:

mm	mm	mm	mm	mm	mm	mm	mm
0.10	0.22	0.36	0.65	1.0	1.8	2.8	5.0
0.12	0.25	0.40	0.70	1.1	2.0	3.2	6.5
0.16	0.28	0.45	0.80	1.3	2.2	3.6	...
0.18	0.30	0.50	0.90	1.4	2.5	4.0	...
0.20	...	0.55	...	1.6	...	4.5	...

X2. STANDARD DENSITIES

X2.1 For purposes of calculating weights, cross sections, and so forth, the densities of the copper alloys covered by the specifications listed in the Scope Section shall be taken as follows:

ASTM Designation	Material	Copper Alloy UNS No.	Density, g/cm ³		
B 36/B 36M	copper-zinc alloy (brass)	C21000	8.86		
		C22000	8.80		
		C23000	8.75		
		C24000	8.66		
		C26000	8.53		
		C26800	8.47		
		C27200	8.44		
		C65100	8.75		
B 96/B 96M	copper-silicon alloy	C65500	8.53		
		C65800	8.53		
		C51000	8.86		
B 103/B 103M	copper-tin alloy (phosphor bronze)	C51100	8.86		
		C52100	8.80		
		C52400	8.77		
		C53200	8.94		
		C53400	8.91		
		C54400	8.86		
		B 121/B 121M	copper-zinc-lead alloy (leaded brass)	C33500	8.47
				C34000	8.47
C34200	8.50				
C35000	8.44				
C35300	8.47				
C35340	8.47				
C35600	8.50				
C70600	8.94				
B 122/B 122M	copper-nickel-zinc alloy (nickel silver and copper-nickel alloy)	C71000	8.94		
		C71500	8.94		
		C72200	8.94		
		C61300	7.59		
		C72500	8.89		
		C73500	8.83		
		C74000	8.69		
		C74500	8.66		
		C75200	8.75		
		C76200	8.58		
		C77000	8.69		


B 248M – 01^{€1}

ASTM Designation	Material	Copper Alloy UNS No.	Density, g/cm ³
B 152/B 152M	Copper UNS Nos. C10100, C10200, C10300, C10400, C10500, C10700, C10800, C12000, C12200, C12300, C11000, C11300, C11400, C11600, C12500, C14530 C14200	...	8.94
		...	8.91
B 169/B 169M	copper-aluminum alloy (aluminum bronze)	C60600	8.17
		C61000	7.78
		C61400	7.59
		C17000	8.22
B 194	copper-beryllium alloy	C17200	8.22
		C66700	8.53
B 291	copper-zinc-manganese alloy	C63800	8.28
B 422	copper-nickel-silicon	C70250	8.82
		C70260	8.87
		C72400	8.59
		C19200	8.87
		C19400	8.91
		C19500	8.92
		C19600	8.87
B 534	copper-cobalt-beryllium alloy	c19700	8.84
		C17500	8.75
		C17510	8.77
B 591	copper-zinc-tin alloys	C40500	8.83
		C40800	8.86
		C41100	8.80
		C41300	8.80
		C41500	8.80
		C42200	8.80
		C42500	8.75
		C43000	8.75
		C43400	8.75
		B 592	copper-zinc-aluminum-cobalt alloy
C69000	8.20		
B 740	copper-nickel-tin alloys	C72700	8.89
		C72900	8.94
		C72650	8.86

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).