



## Standard Test Method for Dilute Solution Viscosity of Vinyl Chloride Polymers<sup>1</sup>

This standard is issued under the fixed designation D 1243; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the determination of the dilute solution viscosity of vinyl chloride polymers in cyclohexanone. The viscosity is expressed in terms of inherent viscosity (logarithmic viscosity number). The test method is limited to those materials that give clear, uniform solutions at the test dilution.

NOTE 1—Other expressions for viscosity may be used as described in the Appendix, but any change from the test method as specified shall be stated in the report.

1.2 The values stated in SI units are to be regarded as the standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 2—Although this test method and ISO 1628-2-1988 differ in approach or detail, data obtained by either are technically equivalent.

### 2. Referenced Documents

#### 2.1 ASTM Standards:

- D 445 Test Method for Kinematic Viscosity of Transparent and Opaque Liquids (and the Calculation of Dynamic Viscosity)<sup>2</sup>
- D 883 Terminology Relating to Plastics<sup>2</sup>
- D 1600 Terminology for Abbreviated Terms Relating to Plastics<sup>3</sup>
- D 1755 Specification for Poly(Vinyl Chloride) Resins<sup>3</sup>
- D 2857 Test Method for Dilute Solution Viscosity of Polymers<sup>4</sup>
- E 77 Method for Verification and Calibration of Liquid-in-Glass Thermometers<sup>5</sup>

#### 2.2 ISO Standard:

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.15 on Thermoplastic Materials (Section D20.15.07).

Current edition approved March 15, 1995. Published May 1995. Originally published as D 1243 – 52 T. Last previous edition D 1243 – 79 (1990) <sup>$\epsilon$ 1</sup>.

This edition contains changes in Sections 1 and 2 to include an ISO equivalency statement.

<sup>2</sup> Annual Book of ASTM Standards, Vols 05.01 and 10.03.

<sup>3</sup> Annual Book of ASTM Standards, Vol 08.01.

<sup>4</sup> Annual Book of ASTM Standards, Vol 08.02.

<sup>5</sup> Annual Book of ASTM Standards, Vol 14.03.

ISO 1628-2-1988 Determination of Viscosity Number and Limiting Viscosity Number—Part 2: Poly(Vinyl Chloride) Resins<sup>6</sup>

2.3 National Institute of Standards and Technology Circular:<sup>7</sup>

C-434 Testing of Glass Volumetric Apparatus

### 3. Terminology

3.1 *Definitions:* Definitions are in accordance with Terminology D 883 and Terminology D 1600, unless otherwise indicated.

### 4. Summary of Test Method

4.1 A sample of resin is dissolved in cyclohexanone to make a solution of specified concentration. Inherent viscosity (logarithmic viscosity number) is calculated from the measured flow times of the solvent and of the polymer solution.

NOTE 3—For additional information, refer to Test Method D 445 and Test Method D 2857 for Dilute Solution Viscosity of Polymers.<sup>3</sup>

### 5. Significance and Use

5.1 Dilute solution viscosity values for vinyl chloride polymers are related to the average molecular size of that portion of the polymer that dissolves in the solvent.

### 6. Apparatus

6.1 *Transfer Pipets.*

6.2 *Volumetric Flasks,* 100-mL, glass-stoppered, in accordance with National Institute of Standards and Technology Circular C-434.

6.3 *Viscometer,* Ubbelohde Series U-1 or Cannon-Ubbelohde No. 75.

6.4 *Water Bath,* at  $30 \pm 0.5^\circ\text{C}$ , controlled to within  $\pm 0.01^\circ\text{C}$ .

6.5 *Timer,* as specified in Test Method D 445, graduated in divisions of 0.1 s or less.

6.6 *Filter Funnel,* fritted-glass.<sup>8</sup>

6.7 *Thermometer,* standard, in accordance with Method E 77.

<sup>6</sup> Available from American National Standards Institute, 11 W. 42nd St., 13th Floor, New York, NY 10036.

<sup>7</sup> Available from National Institute of Standards and Technology, U. S. Dept. of Commerce, Washington, DC 20234.

<sup>8</sup> Filters may be obtained from Corning Glass, No. 36060 “Coarse” type.

## 7. Materials

7.1 *Solvent*—Cyclohexanone, analytical reagent grade or laboratory-distilled technical grade, boiling between 155 and 156°C at 760 mm Hg has been found acceptable if stored in a closed container.

## 8. Procedure

8.1 Dissolve duplicates of resin as follows: Weigh  $0.2 \pm 0.002$  g of the sample (moisture content below 0.1 %) and transfer it to a 100-mL glass-stoppered volumetric flask. Take care to transfer all of the weighed resin into the flask. As an alternative method, the resin ( $0.2 \pm 0.002$  g) may be weighed directly into a tared, 100-mL glass-stoppered volumetric flask.

8.2 Add 50 to 70 mL of cyclohexanone to the flask, taking care to wet the resin so that lumps do not form.

8.3 Heat the flask at  $85 \pm 10^\circ\text{C}$  until the resin is dissolved. Occasional shaking will reduce the time required for solution. Heating should not exceed 12 h and should preferably be less to minimize degradation. If any gel-like particles can be seen, prepare a new solution.

8.4 Cool the solution to the test temperature by immersing flask in the  $30^\circ\text{C}$  bath for a minimum time of 30 min and adjust to a solution volume of 100 mL. Filter through a fritted-glass filter directly into the viscometer.

8.5 Measure at  $30^\circ\text{C}$  the flow time of the prepared solution (8.4) and of the pure solvent (aged at  $85 \pm 10^\circ\text{C}$ ) in the viscometer. Allow 10 min for the viscometer to come to temperature equilibrium after placing it in the water bath. The flow time of the solution or the solvent should be within 0.1 % on repeat runs on the same filling.

NOTE 4—Keep the Ubbelohde viscometer clean when not in use. Acetone may be used as a cleaning flush. The viscometer may be stored filled with pure solvent or it may be stored dry.

## 9. Calculation

9.1 Calculate the relative and inherent viscosity (viscosity ratio and logarithmic viscosity number) as follows:

$$\eta_{\text{rel}} = t/t_o$$

$$\eta_{\text{inh}} = (\ln \eta_{\text{rel}})/C$$

where:

- $\eta_{\text{rel}}$  = relative viscosity (viscosity ratio),
- $t$  = efflux time of the solution,
- $t_o$  = efflux time of the pure solvent,
- $C$  = weight of sample used (8.1) per 100 mL of solution,
- $\eta_{\text{inh}}$  = inherent viscosity (logarithmic viscosity number), and
- $\ln \eta_{\text{rel}}$  = natural logarithm of relative viscosity (viscosity ratio).

## 10. Report

10.1 Report the average inherent viscosity of two analyses to the nearest 0.01.

## 11. Precision and Bias <sup>9</sup>

11.1 An interlaboratory test program utilizing this test method was carried out in 1973 involving seven laboratories, each performing pairs of determinations on one polymer.

NOTE 5—See Specification D 1755, Table 3, for inherent viscosity value of ASTM PVC Reference Standard No. 1.

11.2 *Precision*—The following values of precision have been calculated from the interlaboratory test program at a 95 % confidence level:

Within-laboratory precision (within one pair of values)	1.4 % of mean
Between-laboratories precision (between averages of pairs)	2.2 % of mean

11.3 *Bias*—No justifiable statement of bias can be made for this test method, since the true value of the property cannot be established by an accepted referee method.

## 12. Keywords

12.1 dilute solution viscosity; inherent viscosity; intrinsic viscosity; relative viscosity; specific viscosity; test method; vinyl chloride polymers

<sup>9</sup> Supporting data are available from ASTM Headquarters. Request RR: D20-1112.

## APPENDIX

### (Nonmandatory Information)

#### X1. OTHER EXPRESSIONS FOR VISCOSITY

##### X1.1 Definitions

X1.1.1 *relative viscosity*—ratio of the flow time of a specified solution of the polymer to the flow time of the pure solvent. The International Union of Pure and Applied Chemistry (IUPAC) term for relative viscosity is viscosity ratio.

X1.1.2 *specific viscosity*—relative viscosity minus one. Specific viscosity represents the increase in viscosity that may be attributed to the polymeric solute.

X1.1.3 *reduced viscosity*—ratio of the specific viscosity to the concentration. Reduced viscosity is a measure of the

specific capacity of the polymer to increase the relative viscosity. The IUPAC term for reduced viscosity is viscosity number.

X1.1.4 *inherent viscosity*—ratio of the natural logarithm of the relative viscosity to the concentration. The IUPAC term for inherent viscosity is logarithmic viscosity number.

X1.1.5 *intrinsic viscosity*—limit of the reduced and inherent viscosities as the concentration of the polymeric solute approaches zero and represents the capacity of the polymer to increase viscosity. Interactions between solvent and polymer

molecules have the affect of yielding different intrinsic viscosities for the same polymer in various solvents. The IUPAC term for intrinsic viscosity is limiting viscosity number.

## X1.2 Determination of Intrinsic Viscosity (Limiting Viscosity Number)

X1.2.1 To determine the intrinsic viscosity (limiting viscosity number) of a polymer from dilute solution viscosity data, the reduced and inherent viscosities (viscosity and logarithmic viscosity number) of solutions of various concentrations of the polymer are determined at constant temperature and these values are then plotted against the respective concentrations. The two lines thus obtained converge to a point of zero concentration of the solute which represents the intrinsic viscosity (limiting viscosity number) of the polymer in that solvent at the temperature of the determination. Fig. X1.1 illustrates this convergence.

X1.2.2 At higher concentrations the viscosity curves may deviate from linearity; therefore, the greatest accuracy is

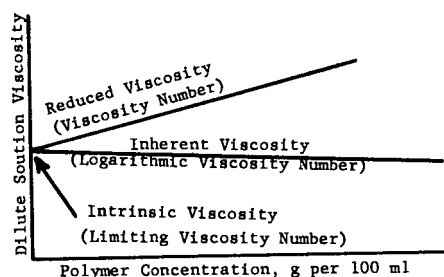


FIG. X1.1 Example of Plot to Determine Intrinsic Viscosity.

obtained at less than 0.5 g/mL of solution. Since extrapolation of either reduced viscosity or inherent viscosity (viscosity or logarithmic viscosity number) curves to infinite dilution will give the same value for intrinsic viscosity (limiting viscosity number), a plot of either type of viscosity will permit the calculation of valid intrinsic viscosity (limiting viscosity number) data.

## X1.3 Estimation of Intrinsic Viscosity (Limiting Viscosity Number)

X1.3.1 The mathematical method of Billmeyer (1)<sup>10</sup> permits a good approximation of intrinsic viscosity (limiting viscosity number). This method makes use of equations derived from the power series expansion of viscosity versus concentration. Neglecting the higher order terms, equations may be written which can be used to estimate intrinsic viscosity (limiting viscosity number). The following equation has been found suitable for poly(vinyl chloride) resins:

$$\eta = \frac{1}{4} [(\eta_{rel} - 1)/C] + \left[ \left( \frac{3}{4} \ln \eta_{rel} \right) / C \right]$$

where  $C$  = concentration of polymer, g/100 mL.

<sup>10</sup> The boldface numbers in parentheses refer to the list of references at the end of this test method.

## REFERENCES

- (1) Billmeyer, F. W., Jr., *Journal of Polymer Science*, Vol 4, 1949, p. 83.
- (2) Cragg, L. H., and Fern, C. R. H., *Journal of Polymer Science*, Vol 10, 1953, p. 185.
- (3) Huggins, M. L., *Journal of the American Chemical Society*, Vol 64, 1942, p. 2716.
- (4) International Union of Pure and Applied Chemistry, *Journal of Polymer Science*, Vol 8, 1952, p. 269.
- (5) Streeter, D. J., and Boyer, R. F., *Industrial and Engineering Chemistry*, Vol 43, 1951, p. 1790.

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.