



Standard Test Method for Permeability of Thermoplastic Containers to Packaged Reagents or Proprietary Products¹

This standard is issued under the fixed designation D 2684; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers procedures for determining the permeability of thermoplastic containers to packaged reagents or proprietary products under specified conditions of exposure. The exposures used are intended to simulate the normal and elevated temperature-storage conditions that might be encountered in end-use application.

1.2 This test method is applicable only to those types of containers designed to allow positive, leakproof closure.

1.3 Two procedures are provided:

1.3.1 *Procedure A* is specific to testing only with a standard design container. This procedure provides for determinations of rate of weight loss (or gain) and for calculation of a permeability factor.

1.3.2 *Procedure B* applies to tests of all other container designs. Permeability data by this procedure are expressed only in terms of rate of weight loss (or gain) for the particular container tested.

1.4 The values stated in SI units are to be regarded as the standard.

NOTE 1—There is no similar or equivalent ISO Standard.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

D 618 Practice for Conditioning Plastics and Electrical Insulating Materials for Testing²

D 1248 Specification for Polyethylene Plastics Molding and Extrusion Materials²

D 1505 Test Method for Density of Plastics by the Density-Gradient Technique²

E 145 Specification for Gravity-Convection and Forced-Ventilation Ovens³

3. Terminology

3.1 Definitions:

3.1.1 *permeability factor, P_t* —the permeability of a given plastic to a given product at temperature t , in degrees Celsius, expressed in units of $\text{g}\cdot\text{cm}/\text{day}\cdot\text{m}^2$, as determined by Procedure A. The permeability factor under 23°C test conditions, for example, is signified by the notation P_{23} .

3.1.2 Determination of P_t is based on an averaged wall thickness over the entire area of the container and an assumption that permeation rate is inversely proportional to the thickness. Precaution in the extent of allowable variations of these factors is recommended, and use of P_t should take into consideration that wall thickness of the containers varies, that the estimate of average thickness from density, area, and weight is not exact, and that permeability of the product through the plastic material may not be directly proportional to the thickness.

4. Summary of Test Method

4.1 Test bottles are filled with the test product and, after sealing, are exposed at 23°C (73.4°F) and 50°C (122°F) conditions for 28 days or longer. Measurements of weight are made at intervals to determine the average rate of weight change.

5. Significance and Use

5.1 With the proper precautions and background experience, results can be useful for estimation of the loss of a packaged product through the walls of a container during shelf storage. The test is also useful for isolating the effects of a container design and materials, and is applicable for development and research and for specification purposes.

5.2 In the absence of adequate supporting data, extrapolations or correlations of results to conditions beyond those of the test are not recommended because of possible product alteration, solvency, or chemical effects on the plastic, etc.

5.3 Before proceeding with this test method, reference should be made to the specification of the material being tested. Any test specimen preparation, conditioning, dimensions, or testing parameters, or combination thereof, covered in the materials specification shall take precedence over those mentioned in this test method. If there are no material specifications, then the default conditions apply.

¹ This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.20 on Plastic Products.

Current edition approved Nov. 10, 1995. Published January 1996. Originally published as D 2684 – 68 T. Last previous edition D 2684 – 89.

² *Annual Book of ASTM Standards*, Vol 08.01.

³ *Annual Book of ASTM Standards*, Vol 14.02.

6. Apparatus

6.1 *Enclosure* or room with provision for maintaining the standard laboratory atmosphere of $23 \pm 2^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and $50 \pm 5\%$ relative humidity, as defined by Practice D 618.

6.2 *Circulating-Air Oven*, consistent with ovens in accordance with Specification E 145, capable of maintaining a temperature of $50 \pm 1^\circ\text{C}$ ($122 \pm 1.8^\circ\text{F}$) and an airflow rate of 8.5 to 17.0 m³/min (300 to 600 ft³/min). The limitation of 25 ft³ on oven size can be overlooked, provided all other requirements are met.

NOTE 2—Only explosion-proof equipment with provision for adequate exhaust of vapors should be used for tests with potentially hazardous or toxic products.

NOTE 3—Relative humidity variation can significantly affect permeability loss in many products, especially water-based products in various thermoplastics. Therefore, the user may find it useful to equip the oven with a means to measure relative humidity and to record the same during the period of test.

6.3 *Balance*, accurate to 0.01 % of the weight of test container and contents.

6.4 *Container Seals*, suitable heat-sealing laminate⁴ and polyethylene or other suitably lined screw-type closures for sealing the containers.

6.5 *Heat Sealer*.⁵

6.6 *Torque Wrench*.⁶

7. Reagents and Materials

7.1 The reagent or proprietary product as specified for testing.

8. Test Specimens

8.1 The test specimen for Procedure A shall be the 4-oz cylindrical bottle design as specified in Fig. 1, having a nominal external surface area of 154 cm² (23.8 in.²).

8.2 The test specimen for Procedure B may be any thermo-plastic container, as specified or selected for test evaluation, provided it is designed to allow positive closure.

8.3 For each procedure, a minimum of three specimens shall be tested at each temperature. Three additional specimens are required for Procedure A for determination of the plastic density.

NOTE 4—Trim and finish the containers, if needed, to ensure a smooth contacting surface for positive seal.


9. Conditioning

9.1 *Conditioning*—Condition the test specimens at $23 \pm 2^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and $50 \pm 5\%$ relative humidity for not less than 40 h prior to test in accordance with Procedure A of Practice D 618, for those tests where conditioning is required. In cases of disagreement, the tolerances shall be $\pm 1^\circ\text{C}$ ($\pm 1.8^\circ\text{F}$) and $\pm 2\%$ relative humidity.

⁴ One such laminate suitable for polyethylene containers, MIL-B-131C Class 2, a polyethylene-aluminum foil-paper laminate available from the Robertson Co., Jamaica, NY. Heat sensitive seals are also available from 3M Packaging Systems Division, 3M Center Building 220-8W-01, St. Paul, MN, 55144.

⁵ Super Sealer made by Ciamco Corp., 12900 Plaza Dr., Cleveland, OH 44130 is suitable.

⁶ Model 25 Owens-Illinois Torque Tester, Model MRA available from Secure Pak, Inc., P.O. Box 14499, Toledo, OH 43614 is suitable.

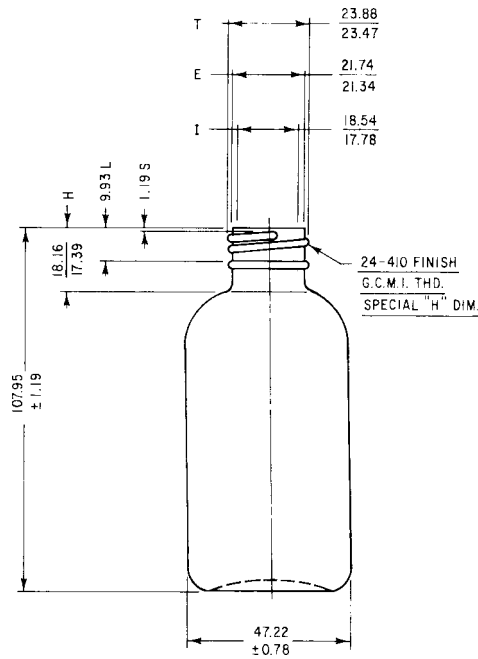

NOTE 1—Dimensions are in millimetres.
FIG. 1 Standard Container for Permeability Test

9.2 *Test Conditions*—Conduct tests in the standard laboratory atmosphere of $23 \pm 2^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and $50 \pm 5\%$ relative humidity, unless otherwise specified in the test methods. In cases of disagreements, the tolerances shall be $\pm 1^\circ\text{C}$ ($\pm 1.8^\circ\text{F}$) and $\pm 2\%$ relative humidity.

10. Procedure A (Standard Container)

10.1 With specimens taken from the sidewalls of three of the containers, determine the average plastic density by Test Method D 1505, or by an alternative method of equivalent accuracy.

10.2 For each test temperature, select a minimum of three containers. Weigh each when empty, without the closure. Also weigh the empty containers with their corresponding closures and appropriately sized laminate pieces.

10.3 Fill the containers to nominal capacity with the test product.

10.4 Make a thorough check for any drippage or spill of product on the outside surface of the containers. If any is noted, replace the container with a new specimen.

10.5 Heat seal the containers with the laminate (plastic to plastic), check for leaks, and then cap the containers with screw-type closures, using sufficient torque to provide positive seal. Avoid distorting the container when capping.

NOTE 5—One method of testing for a poor seal is to immerse an upright test container in a beaker filled to the base of the cap with a liquid that will not attack the plastic. When a vacuum of 15 in. Hg is applied to the entire system, a poorly sealed bottle will give off bubbles from the sealed area.

NOTE 6—Any deformation of the container during sealing may result in a volume change which will affect the final test pressure. An application torque of 1.7 N·m (15 lbf·in.) has been found sufficient for the standard container in Fig. 1.

10.6 Weigh the sealed containers.

10.7 Unless otherwise specified, expose one set of containers in the Standard Laboratory Atmosphere, $23 \pm 2^\circ\text{C}$ ($73.4 \pm$

3.6°F) and $50 \pm 5\%$ relative humidity, and another set in a circulating-air oven controlled at $50 \pm 1^\circ\text{C}$ ($122 \pm 1.8^\circ\text{F}$). Place the containers upright on an inert metal screen or perforated sheet support to allow air circulation. Place a tray beneath the container support to collect leakage of product, if failure occurs. Provide enough spacing between the containers so they do not touch each other. Also, take precautions as necessary to prevent any possible cross-contamination in the test chamber from other agents.

NOTE 7—For certain relatively unstable or spoilable products, the use of elevated temperature exposures may not be applicable.

10.8 Weigh the containers after 1 day, 7 days, 14 days, 21 days, and 28 days. In certain cases, a steady rate of weight change may be reached in either a shorter or longer period. Other intervals can then be used. They should be regular and reported.

10.8.1 If the weight change appears abnormal for any of the containers during exposure, inspect the containers to ensure that a positive seal exists. If a leak is detected, retest with a new specimen.

10.8.2 Cool in the standard laboratory atmosphere until consistent weighings are obtained. Resume oven exposure within 6 h from removal time.

10.8.3 In elevated-temperature tests, rotate the locations of the specimens in the oven when re-exposing after each interval to minimize possible bias due to variations of airflow and temperature within the oven.

10.9 Calculation:

10.9.1 Calculate the percentage weight loss or gain after a given exposure time as follows:

$$\text{Weight loss (at time } x), \% = [(G_u - G_x)/N_u] \times 100 \quad (1)$$

$$\text{Weight gain (at time } x), \% = [(G_x - G_u)/N_u] \times 100 \quad (2)$$

where:

G_u = gross weight of unexposed bottle, closure, and contents, g,

G_x = gross weight of exposed bottle, closure, and contents, g, and

N_u = net weight of unexposed test product in the bottle, g.

10.9.2 *Rate of Average Weight Change*—Plot the weight changes, $G_u - G_x$ for losses or $G_x - G_u$ for gains, versus time in days on rectilinear graph paper. Draw the best straight line through the points, ignoring, if necessary, points near the beginning or end of the test period that deviate excessively from the best line through intermediate points. From the slope of the line, determine the rate of average weight change, R , in grams per day, as illustrated in Fig. 2. Note whether the change is loss or gain.

$$\text{Weight change per day, \%} = (R/N_u) \times 100 \quad (3)$$

10.9.3 *Permeability Factor* (see 3.1)—Calculate the permeability factors as follows:

$$P_t = RT/A \quad (4)$$

For P_t in metric units, $\text{g}\cdot\text{cm}/\text{day}\cdot\text{m}^2$.

R = rate of average weight change, g/day, from 10.9.2, and
 T = average bottle wall thickness, cm, calculated from bottle weight, area in cm^2 , and density of the bottle material, for example:

$$T = \frac{\text{weight of bottle (g)}}{\text{density (g/cm}^3) \times \text{area (cm}^2)} \quad (5)$$

A = bottle surface area, m^2 .

NOTE 8—For Procedure A, where the standard 4-oz Boston Round Bottle is used (23.8-in.² area), the following equations can be used:

To calculate P_t in metric units:

$$P_t = \frac{RT/A = R (\text{g/day}) \times \text{weight of bottle (g)}}{\text{density (g/cm}^3) \times 2.358} \quad (6)$$

11. Procedure B (Nonstandard Containers)

11.1 Follow the procedure in 10.2-10.8.

NOTE 9—If not feasible to heat seal the container due to design, etc., any other means for providing an equivalent, nonpermeable, leakproof closure would be an acceptable alternative.

11.2 Calculation:

11.2.1 Calculate the percentage weight loss or gain after a given exposure time as detailed in 10.9.1.

11.2.2 Calculate the rate of average weight change as shown in 10.9.2.

12. Report

12.1 Report the following information:

12.1.1 Complete bottle and test product identification and description,

12.1.2 Complete closure identification and description.

12.1.3 Exposure conditions,

12.1.4 Calculated permeation data,

12.1.5 Any occurrences of container leakage, failure, etc.,

12.1.6 Date of test,

12.1.7 Duration of test, and

12.1.8 Regular weighing intervals.

13. Precision and Bias

13.1 Round-robin testing⁷ among six laboratories by Procedure A was performed with containers of Type I polyethylene in accordance with Specification D 1248, and a variety of liquid reagents. P_t values ranged from 0.02 to about 200 $\text{mg}\cdot\text{cm}/\text{day}\cdot\text{m}^2$. Over this wide range, the standard deviations of the results between laboratories increased with increased values of P_t . For 18 levels of P_t , the interlaboratory coefficients of variation remained relatively constant with the overall average being 14 %.

13.2 Since there is no accepted reference method for this test method, the bias of this test method cannot be determined.

14. Keywords

14.1 containers; permeability; plastic bottles

⁷ Supporting data have been filed at ASTM Headquarters. Request RR:D20-50.

$$\begin{array}{r} \text{(A) AT 22 DAYS} = 2.28 \text{ GM} \\ \text{(B) 2 DAYS} = 0.28 \text{ GM} \\ \hline 20 \text{ DAYS} = 2.00 \text{ GM} \\ \text{AVG. RATE} = \frac{2.00}{20} = 0.10 \text{ GM/DAY} \end{array}$$

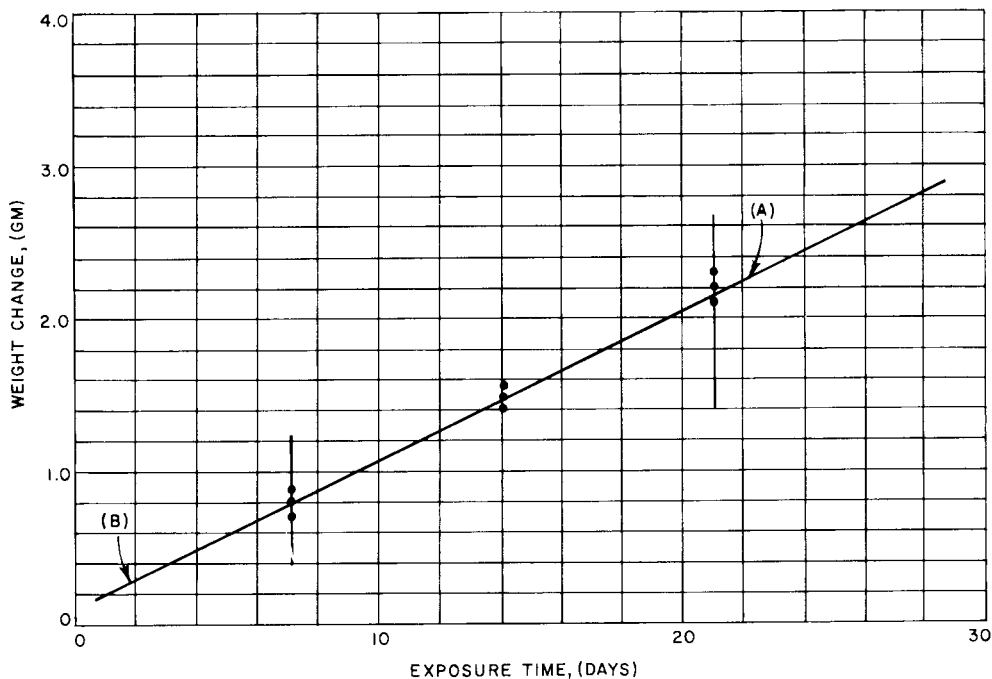


FIG. 2 Example Plot—Determination of Slope for Rate of Weight Change

APPENDIX

(Nonmandatory Information)

X1. MIXED INCH-POUND METRIC UNITS AND CONVERSION FACTORS

X1.1 For P_t in mixed inch-pound-metric units, g-mil/day·100 in.².

R = rate of average weight change, g/day, from 10.9.2,
 T = average bottle wall thickness, mil, calculated from bottle weight, area in in.², and density, for example:

$$T = \frac{\text{weight of bottle (g)} \times 1000 \text{ (mil/in.)}}{\text{density (g/cm}^3\text{)} \times 16.39 \text{ (cm}^3\text{)} \times \text{area (in.}^2\text{)}} \quad \text{(X1.1)}$$

A = bottle surface area in units of 100 in.²; for example, if bottle surface area is 23.8 in.², $A = 0.238$.

NOTE X1.1—The mixed inch-pound-metric units are not recommended for general use, but are included to establish a relationship with work that has been previously accomplished in this area.

X1.2 To convert P_t values between systems use the following equations:

$$P_t \text{ (metric units)} = 0.0394 P_t \text{ (mixed inch-pound-metric units)}$$

$$P_t \text{ (mixed inch-pound-metric units)} = 25.4 P_t \text{ (metric units)}$$

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.

This standard is copyrighted by ASTM, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (<http://www.astm.org>).